


General InformationBody Repair, Body Collision Repair



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.







Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



Technical information should always be available to the foremen and mechanics, because their careful and constant adherence to the instructions is essential to ensure vehicle road-worthiness and safety. In addition, the normal basic safety precautions for working on motor vehicles must, as a matter of course, be observed.

All rights reserved.

No reproduction without prior agreement from publisher.

Contents

1	Training/Personnel Qualification	1
1.1	Qualification	1
2	Safety Precautions	2
2.1	Safety Precautions	2
2.2	Safety Precautions when Working on Cooling System	4
2.3	Safety Precautions during Road Test with Testing Equipment	5
2.4	High-Voltage Components / Electric Vehicles	5
3	Repair Information	6
3.1	Notes for Working with Fine, Aluminum and Steel Dust	6
3.2	Adhesive Surfaces for Adhesive Tape	7
3.3	Secured Threaded Connections	7
3.4	Identification Plates	7
3.5	Impact Wrenches	7
3.6	Multi-Material Mix	8
3.7	Removal Method on Multi Material Body Repair Station	8
3.8	Battery, Voltage Supply	9
3.9	A/C System / Refrigerant	9
3.10		10
4	Body Repair General Information ´	11
4.1	Original Joint	11
4.2		11
4.3	Remaining Material, Removing ´	11
4.4	New Parts	11
4.5	Molded Foam Parts	12
5	Explanation of Symbols	13
5.1		13
5.2		13
5.3		14
5.4	Symbols for Preparation	15
5.5	Symbols for Preparation Symbols for Ocion Symposis and Commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG does not guarantee or accept any liability	16
6	Construction Characteristics of Vehicle Body. Copyright by AUDI AG.	18
6.1	· · · · · · · · · · · · · · · · · · ·	18
7		19
7.1		19
7.2		19
7.3	,	19
7.4		22
7.5		23
7.6		29
8		32
8.1	· · · · · · · · · · · · · · · · · · ·	32
8.2	· · · · · · · · · · · · · · · · · · ·	33
8.3		34
8.4		34
8.5	· · · · · · · · · · · · · · · · · · ·	35
8.6	· · · · · · · · · · · · · · · · · · ·	36
8.7		37
8.8	· · · · · · · · · · · · · · · · · · ·	37
8.9	· · · · · · · · · · · · · · · · · · ·	37
9	·	39
9.1	•	40
10	, ,	52
10	Our committee to contract the contract to the	1

(~	
_	_		_

10.1	Rivets	52
10.2	Flow-Drill Bolts	59
10.3	Clinching	61
11	Separation Technologies in Body Repair; Application	62
11.1	Drilling	62
11.2	Sawing	62
11.3	Sanding	62
11.4	Milling	62
12	Surface Repairs	64
12.1	Dent Removal Techniques, Steel Panel	64
12.2	Dent Removal Procedures, Aluminum Panel	65
12.3	Metal and Aluminum Body Filler, Handling	66
12.4	Unleaded Tin, Handling	67
12.5	"Accurately Contoured Surface" Definition, Transfer to Paint Shop	67
13	Straightening Procedures on Vehicle Structure	68
13.1	Straightening	68
13.2	Separating Cuts	68
13.3	Body Sub-Parts and Partial Sections	68
14	Corrosion Protection	69
14.1	Corrosion Protection on Attachments and Welded Parts	69
14.2	Sealing Cavities	69
15	Plastic Repair	71
15.1	Dents, Servicing	71
15.2	Scratches, Servicing	73
15.3	Cracks, Servicing, Up to 100 mm Long	74
15.4	Holes, Servicing, Up to 30 mm Diameter	75
15.5	Plastic Repair (GFK)	76
16	Glass Repair	80
16.1	Windshield Repair	80
16.2	Required Special Tools and Testing Equipment	84
16.3	Repair Description	86
17	Thread Repairs	91
17.1	Thread Repairs on Safety-Related Components	91
17.2	Threads on Subframe Fastener, Servicing	91
17.3	Helicoil Plus Twinsert	98



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



1 Training/Personnel Qualification

(Edition 07.2021)

001.KAH0.00.21 - FU 07.2021 10/08/2021 JY

⇒ 1.1 , page 1

1.1 Qualification

To be able to perform a perfect and process-safe repair in the workshop, the following vehicle specific training modules are required.

Refer to \Rightarrow Rep. Gr. 00; Training/Personnel Qualification; Qualification.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





2 Safety Precautions

- ⇒ P2.1 recautions", page 2
- ⇒ P2.2 recautions when Working on Cooling System", page 4
- ⇒ P2.3 recautions during Road Test with Testing Equipment", page 5
- ⇒ C2.4 omponents / Electric Vehicles", page 5

2.1 Safety Precautions

Follow all country-specific regulations regarding accident prevention and safety on the workplace.

Welding and sanding must always be carried out with Ventilation System.



WARNING

Risk of explosion due to dust concentration and aluminum and steel when sanding and separating.

There is a risk of fatal or serious bodily injury due to an explosion.

- Check and clean the exhaust extraction system before beginning work on the functions.
- Extract accumulating sanding dust with the respective permitted vacuum cleaner for the material. Protected by Copyright Cop
- Always separate the dust from different materials (separeur rate aluminum steel and carbon fiber-reinforced polymer (CFRP)).
- Keep the work station free of aluminum and steel dust. Remove the dust accumulation.
- Do not blow out the accumulated with compressed air.
- Never weld and sand in the same room at the same time.
- To prevent external sparks, if possible use only air driven sanding and removal devices.
- Empty the extraction system after using.
- Prevent water and moisture when separating and sanding.

⇒ f3.1 or Working with Fine, Aluminum and Steel Dust", page

Composite Material Safety Precautions (Carbon Fiber-Reinforced Polymer (CFRP))

⇒ N7.5.5 otes for Carbon Fiber-Reinforced Polymer (CFRP)", page 25

Risk due to hazardous gases.

Sparks are created when welding and separating. If the sparks touch foamed areas within the body hazardous gases will be created.

 Do not perform welding or separating with spark producing devices or tools in the near of foamed areas. g for private or commercial purposes, in part or in whole, is not AUDI AG. AUDI AG does not guarantee or accept any liability ss of information in this document. Copyright by AUDI AG.

WARNING

Risk of the fuel tank or fuel-carrying components exploding due to sanding, welding or separating.

Severe injuries and burns are possible.

When sanding, welding or separating near the fuel system remove the fuel tank or fuel-carrying components.

DANGER

There is a risk of explosions and fatal injuries due to damaged natural gas tanks.

The natural gas tank must be checked for damage if components in the real side of real area are removed due to aren damage, such as the bumper cover, rear lid, underbody trim panels, longitudinal members, rear lid end piece, etc.

part or in whole, is not e or accept any liability yright by AUDI AG.

Check for damage on fuel tanks. Refer to ⇒ Natural Gas System - General Information; Rep. Gr. 20; Fuel Tanks, Checking for Damage.



CAUTION

Risk of injury due to flying metal shavings.

Irritation and injury to skin and eyes possible.

- Wear protective eyewear.
- Wear safety gloves.



CAUTION

Health risk due to dusts possible.

Irreversible deposit of dust particles in the lungs. Breathing impairments possible from sanding and separating work.

- Wear a dust mask.
- Use proper extraction.
- No cutting procedures on carbon fiber-reinforced polymer (CFRP) materials.



CAUTION

If welding, soldering or cutting with spark-producing tools in foamed areas hazardous gases are produced.

- Never weld, solder or separate within 15 mm of molded foam parts.
- Perform the procedures with extraction.

Welding and sanding must be carried out with ventilation.

Never weld and sand in any area at the same time.

Clean the work area regularly depending on the amount of dust.

Do not blow out the accumulated with compressed air.

Empty the extraction system after usage.

Follow all country-specific regulations regarding accident prevention and safety on the workplace.



Bonded Joints, Detaching

Body bonded joints can be detached by applying heat. The adhesives used in the vehicle construction and the repair are destroyed at temperatures 180 – 200°C.



Note

- Wear protective gloves and eyewear.
- Avoid direct contact of the adhesives with the skin.

 Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability Avoid inhaling solvent vapors. with respect to the correctness of information in this document. Copyright by AUDI AG.
- Only process adhesives in well-ventilated areas.
- Always note the hazard information from the manufacturer.
- Also note the accident prevention regulations applicable in the respective country.
- Note the corresponding safety data sheets for the adhesive.
- Use suitable extraction.

Galvanized Body Parts



CAUTION

When welding zinc-coated sheet steel panels, toxic zinc oxide develops in the welding emissions.

Perform the procedures with extraction.

2.2 Safety Precautions when Working on Cooling System

There is a risk of scalding due to hot coolant.

The cooling system is under pressure when the engine is warm. There is a risk of scalding due to hot steam and hot coolant.

- Wear safety gloves.
- Wear protective eyewear.
- Reduce the pressure by covering the coolant expansion tank cap with a cloth and carefully opening it.

There is a risk of injury due to an activated parking heater and A/C.

The parking heater and A/C can switch on unintentionally on electric and hybrid vehicles with an activated parking heater and A/C. Body parts can be pinched or pulled in if the radiator fan starts running by itself.

Deactivate the parking heater and A/C.



2.3 Safety Precautions during Road Test with Testing Equipment

There is a risk of injury due to unsecured testing equipment.

If the front passenger airbag activates during a collision, unsecured testing equipment becomes a dangerous projectile.

Secure testing equipment on the rear seat.

or

 Have a second person operate testing equipment on the rear seat.

2.4 High-Voltage Components / Electric Vehicles

There is a risk of fatal injury due to high voltage

The high-voltage system is under high voltage. Electrocution by direct contact or electric arc can cause fatal or serious bodily injury if high-voltage components and high-voltage cables are damaged.

- Visually inspect the high-voltage components and the high-voltage cables.
- Never use cutting, shaping, or sharp-edged tools near high-voltage components and high-voltage cables.
- Never weld, solder, or use thermal bonding or hot air near high-voltage components and high-voltage cables AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

3 Repair Information

- ⇒ f3.1 or Working with Fine, Aluminum and Steel Dust", page 6
- ⇒ S3.2 urfaces for Adhesive Tape", page 7
- ⇒ T3.3 hreaded Connections", page 7
- ⇒ P3.4 lates", page 7
- ⇒ W3.5 renches", page 7
- ⇒ M3.6 ix", page 8
- ⇒ M3.7 ethod on Multi Material Body Repair Station", page 8

3.1 Notes for Working with Fine, Aluminum and Steel Dust

Separation of Aluminum and Steel Dust

All emissions of the new lightweight materials fall under the hazardous materials ordinance (national regulations). These require, independently from all repair quality related guidelines by the vehicle manufacturer, a risk analysis by the company performing the repair.

The employers may permit work with hazardous substances on ses, in part or in whole, is not ly after, a risk assessment has been performed and the required rante or accept any liability safeguard measures have taken place ctness of information in this document. Copyright by AUDI AG.

This means in the specific case, each repairing workshop is legally obligated to create such risk assessment, before the procedures are started or continued.

Fine Aluminum Dust

Physical:

 Aluminum dust is combustible and depending on the particle size and concentration, explosive

Chemical:

- Aluminum dust and water produce a combustible/explosive hydrogen gas
- Aluminum dust + ferric oxide (rust) react under heat with each other (exothermic redox reduction)
- Aluminum dust + ferric oxide + strong ignition sources can at a mixture ratio of 1:3 cause a thermal reaction. This metal fire burns at a temperature of up to 2400 °C and cannot be extinguished with water.
- Aluminum dust is a hazardous material and must be properly extracted according to the local regulations.

Fine Steel Dust

Physical:

- Steel particles can be statically charged and even cold can become an ignition source for the aluminum dust.
- Flying sparks from steel processing provides the perfect ignition source for aluminum dust.
- When performing a sandwich cut through steel and aluminum the explosive aluminum dust and also the ignition source emerge at the same time.

Chemical:

- Aluminum dust + ferric oxide (rust) react under heat with each other (exothermic redox reduction)
- Aluminum dust + ferric oxide + strong ignition sources can at a mixture ratio of 1:3 cause a thermal reaction. This metal fire burns at a temperature of up to 2400 °C and cannot be extinguished with water.

3.2 Adhesive Surfaces for Adhesive Tape

- The vehicle must be at room temperature before installing, for example self-adhesive covers, door seals, etc. with adhesive tape.
- ♦ The adhesive surfaces on the body must be free of dust and commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.
- Clean the adhesive surfaces using Cleaning Solution -D 009 401 04-.
- After installing, press on the covers with adhesive tape using a roller.
- After installing, pull on the components by hand to check for a secure fit.

3.3 Secured Threaded Connections

Installed bolts that are »microencapsulated« must be replaced, and the threaded holes must be cleaned with a suitable thread tap.

3.4 Identification Plates

When replacing vehicle components, the existing identification plates on the old parts that indicate the replacement part number (refer to ⇒ Electronic Parts Catalog (ETKA)), must be applied to the new part according to the specifications.

3.5 Impact Wrenches

Removing bolts and nuts using an impact wrench is generally permitted. The exception to this are procedures within an open high-voltage battery. Generally no impact wrench is permitted for these procedures.

If the following requirements are met, using an impact wrench to tighten bolts and nuts is permitted during repair procedures. Electric and compressed air impact wrenches are generally intended here.

Requirements:

- Bolts with locking fluid or self-locking nuts must only be screwed in at low speeds.
- Use a suitable impact wrench with an adjustable speed and torque range.
- Use suitable screwdriver bits near delicate surfaces. For example, use plastic-coated bits on aluminum rims.
- Refer to the Natural Gas Fuel Systems General Information repair manual when working in a natural gas fuel system area.

Application:

- · Position the bolts or nuts by hand.
- Only tighten the bolts or nuts with an impact wrench until the head of the bolt or nut contacts the surface and then tighten further using a torque wrench.
- Clean the threaded pins before removing the bolt or nut.

3.6 Multi-Material Mix

In addition to the traditionally pure steel body, there is an increase in mixed-material body construction. This means that a combination of various materials are being used together.

The most common materials in modern vehicle bodies are:

- Steel (in varying strengths)
- ◆ Aluminum
- ♦ Magnesium
- Plastics
- ◆ Fiber-reinforced plastic
- Carbon fiber materials

3.7 Removal Method on Multi Material Body Repair Station



Note

- ◆ The Ruwac NA35 Wet Collection for Explosive Materials (VAS6572/1) and the VAS6572/2 must be emptied before and after every operational use.
- ◆ Pay attention to the safety precautions. Refer to ⇒ Body Repair; Rep. Gr. 00; Safety Precautions.

Fine Aluminum Dust

Fine aluminum dust is combustible and/or explosive. Technical equipment must be handled so that no external ignition sources can pass into the filter or the dust collection container. The stationary "genuine" aluminum vacuum stations used through 2009 (Dansk Klimablock / Aeroweld or Nederman) do not offer the mercial purposes, in part or in whole, is not technical equipment protection and also cannot be retrofitted, this document. Copyright by AUDI AG. All these suction devices and the aluminum vacuum devices available on the market are without exception "ignition source free". For this reason vehicles with steel parts and on which flying sparks from the steel components cannot be completely prevented must NOT be worked on in this area.

The Ruwac NA35 Wet Collection for Explosive Materials VAS6572/1 (dust class M) from 2009 and the VAS6572/2 (dust class H) have a 3-part protection against the intake of friction sparks from the possible steel processing. This protection is made of a 5 m long antistatic suction hose, the so-called spark trap and a 5 m long flow calming section. This ensures that also by unintentional sanding of steel components the glowing sparks are cooled well below the ignition temperature of the aluminum dust. The system has the German Technical Inspection

Agency certificate for considerably hotter and longer glowing steel sparks.

A second risk is the static charging of metal particles due to friction in the hoses and pipes during the suction process. This static charge can function as an ignition source in the same way as a glowing spark. To make sure that only the antistatic so called "Ohm hoses" can be installed, the suction system connection coupling and the hoses on the suction side have an error safe Storz-C coupling.

The third risk is the suction device's possible impact as an ignition source on the surrounding area. Because this suction device is based on industrial vacuum cleaners it automatically has all constructive features for the use in zone 22 and to prevent a possible impact as an ignition source in the working environment. For accident repairs the work procedures such as cutting, grinding and welding automatically produce more ignition sources than a suction device can.

Fine Steel Dust

Steel sparks and dust are considered to be risk free. In multi material mixed work stations the steel flying sparks present the greatest risk potential for the fine aluminum dust! For this reason and in compliance with the process separation, a steel vacuum must always be provided which is also allocated to always remain at the body work station. Generally only aluminum vacuums are used because they have a tested spark trap, that could be equal to the explosion protection device heat test, while the vacuum sits next to the worker in the work area during this procedure. The Ruwac NA35 Wet Collection for Explosive Materials VAS6571/1 is based on the same basic machine as the VAS6572/2, but without a 3-part spark trap. It is suitable for use in zone 22. The filter is dust class "M" like those suitable for the metal dust.

3.8 Battery, Voltage Supply



Note

Make sure the radio code is available before disconnecting the battery. Before giving the vehicle to the customer, enter the correct code number to make the radio ready to play.

Before welding. You must remove both battery terminal clamps liability and cover both battery terminals mation in this document. Copyright by AUDI AG.

You must remove the vehicle battery before performing work near the battery that could produce sparks.

3.9 A/C System / Refrigerant

Never weld or hard/soft solder components of a filled A/C system. This also applies to welding and soldering on the vehicle, if there is a risk that it may heat up components in the A/C system. When performing paint repairs, objects in the drying oven or its pre-warming area may only reach 80 °C. This is because warming causes high pressure to develop in the pressure relief valve on the A/C compressor.



Note

Coolant systems must also be extracted if electrical welding will take place around coolant lines. When welding electrically, invisible ultraviolet rays are released that penetrate the coolant hoses and damage the coolant.



3.9.1 Corrective Measure:

Evacuate the refrigerant circuit. Refer to ⇒ Heating, Ventilation and Air Conditioning; Rep. Gr. 87; Heating and A/C System

3.10 Electronic Control Modules

Connect electric welder ground (GND) connector directly to the piece to be welded. When doing so, be careful that there are no electrically insulated parts located between the ground connection and the welding location.

Do not touch electronic control modules and electrical wires with the ground connection or welding electrode.

Replacing electronic control modules after a collision is then only required if at least one of the following conditions is met:

- ♦ The housing is distinguishably deformed or damaged.
- The contact surface or bracket is deformed; the device shows no damage on the outside.
- The connector is damaged or corroded by moisture.
- The function test or OBD of the device shows the fault: "Control module faulty".

If electronic components, for example the ABS control modules, are removed for repair work and then reinstalled, then the existing data must be checked for function after assembly using OBD, for example.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



4 Body Repair General Information

When repairing, the original joint should always be restored.

Standard repairs are described in the repair manual. Further descriptions are not given because if there are more extensive repairs, the damaged area should be removed at the original joint. Where this is possible, the joining techniques can be implemented according to the preceding comparison.

All repairs with special separating cuts and joining techniques that do not correspond to the original joint (production status) are checked and approved by the echnical development team by evaluating, strength testing and crash testing.

- ⇒ J4.1 oint", page 11
- ⇒ B4.2 ody Parts", page 11
- ⇒ M4.3 aterial, Removing", page 11
- ⇒ P4.4 arts", page 11
- ⇒ F4.5 oam Parts", page 12

4.1 Original Joint

"Original joint" refers to a connection that was created by the vehicle manufacturer.

These connections should be reconstructed when performing body repairs.

When doing so, ensure that the production number of weld points does not fall short when making repairs.

Methods and procedures differing from the original connection are described in the applicable body repair manual.

4.2 Galvanized Body Parts

Fully galvanized body parts enable a high level of corrosion protection in body. To maintain the warranty against perforation corrosion even if a repair is required, then the procedures in chapter <u>> P14 rotection</u>", page 69 must be followed precisely.

4.3 Remaining Material, Removing

If the damaged body part is cut out roughly, for example using a body saw, based on the separation cuts in the corresponding repair manual, then have most of the spot-welded bonded joints drilled out with the spot weld breaker.

In addition, we recommend the degree sander as well as an angle grinder to remove the weld connections that cannot be removed with the spot weld breaker.

4.4 New Parts

New parts that are no longer accessible after the repair, for example the side sill, should have corrosion protection installed on them before welding for corrosion protection reasons. It is advisable to cover the welding flange when doing so.

Additional information can be found in the paint manual.

Check new replacement parts, such as doors, panels or fendele, is not ers for transport damage before sending to paint shop. This any liability prevents double painting, if transport or accident damage to the vehicle is noticed during assembly.

4.5 **Molded Foam Parts**

The molded parts are installed in the body shell and increase in volume after priming them in the paint drying-oven from approximately 180 °C.

When using molded foam parts, proceed as follows:

- Remove any remaining foam from the vehicle.
- Create the paint structure according to the paint manual.

⇒ 4.5.1 , page 12

⇒ F4.5.2 oam Part, Replacing", page 12

4.5.1 **Prerequisites**

Before inserting a molded foam part, the metal part to be replaced must be prepared so that it is ready for installation, for example, cutting, fitting, corrosion protection measures.

Molded Foam Part, Replacing 4.5.2

- Cover the molded foam part all around with butyl sealing cord or two-part filler foam.
- Secure the molded foam part on the vehicle.
- Secure the new part (for example, A-pillar) while gently pressing on it around the molded foam part until it makes contact and then weld it in.
- Do not perform gas-shielded welding within at least 40 mm next to the molded foam part (on both sides)
- After painting the vehicle, seal the cavities in the repair area.




Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



5 **Explanation of Symbols**


- ⇒ f5.1 or Removing Components", page 13
- ⇒ f5.2 or Welding and Soldering", page 13
- ⇒ f5.3 or Rivets", page 14
- ⇒ f5.4 or Preparation", page 15
- ⇒ f5.5 or Corrosion Protection", page 16

Symbols for Removing Components 5.1

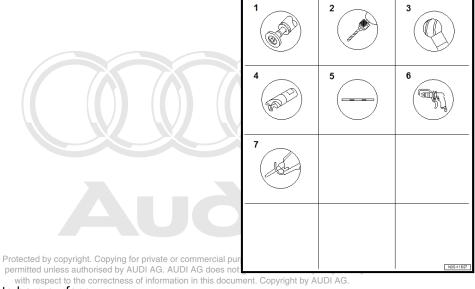

- 1 Grinding / Grinding down to bare surface
- 2 Drilling
- 3 Ball nose end mill
- 4 BTR milling
- 5 Separation Cut
- 6 Loosening weld spots
- 7 Sawing
- Symbols for Welding and Soldering 5.2

- Αυδι
- 1 Stitch Weld Seam
- 2 Gas-Shielded Arc Plug Weld
- 3 Gas-Shielded Arc Continuous Weld Seam
- 4 Gas-Shielded Arc Continuous Weld Seam (Staggered)
- 5 Brazing
- 6 MIG Brazing
- 7 Resistance Spot Welding General
- 8 Straight-Line Spot Weld (Single Řow)
- 9 Straight-Line Spot Weld (Double Row)
- 10 Straight-Line Spot Weld (Double Row, Staggered)

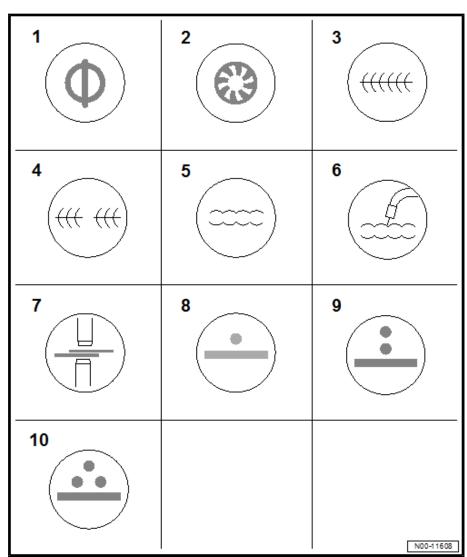


Symbols for Rivets 5.3



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.




- 1 Solid Rivet
- 2 Punch Rivet
- 3 Use Rivet Pliers
- 4 Pop Rivet

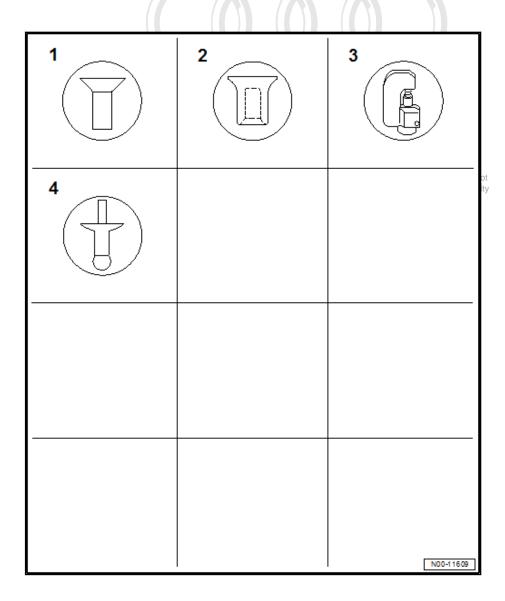

5.4 Symbols for Preparation


- 1 Clamping
- 2 Setting
- 3 Removing Paint on Hard-To-Reach Areas
- 4 Sanding by Hand
- 5 Applying Adhesive
- 6 Setting
- 7 Flanging

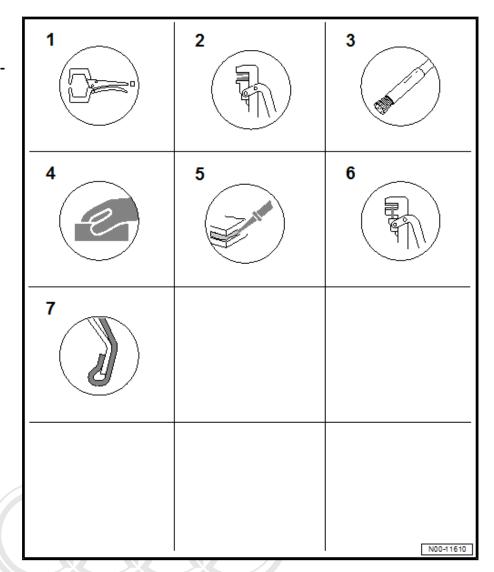

Symbols for Corrosion Protection 5.5

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



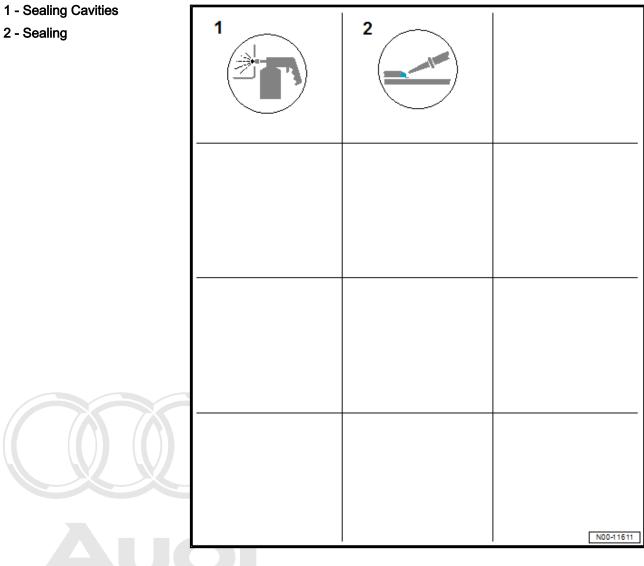

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





Construction Characteristics of Ve-6 hicle Body

⇒ o6.1 f Body Construction", page 18

6.1 Types of Body Construction

In addition to the familiar unitary vehicle body, other types of body construction are used in Volkswagen Group vehicles.

⇒ S6.1.1 paceframe", page 18

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

⇒ V6.1.2 W Amarok (NOT FOR NORTH AMERICAN MAR-**KET)**", page 18

6.1.1 Aluminum Spaceframe

The unique characteristic of the spaceframe body is that it has a supporting frame construction made from aluminum, which ensures the stiffness of the body. Body shell components, such as roofs or fenders, also assist in this, but they generally do not have a supporting function (for example, Audi R8).

Body-On-Frame, VW Amarok (NOT 6.1.2 FOR NORTH AMERICAN MARKET)

Vehicles with body-on-frame construction generally have a supporting ladder frame construction that carries the engine, suspension and body. This type of construction is primarily used in commercial vehicles and off-road vehicles.

7 Damage, Evaluating

- ⇒ I7.1 nformation", page 19
- ⇒ S7.2 eams and Cast Joints, Checking", page 19
- ⇒ P7.3 aths", page 19
- ⇒ /7.4 Damage Diagnosis", page 22
- ⇒ o7.5 f Materials Used", page 23
- ⇒ S7.6 afety Systems", page 29

7.1 General Information

When repairing vehicles involved in collisions, damage to the body or suspension is not discovered. In some cases, this may cause serious subsequent damage later. In accidents that indicate a heavy load on the vehicle, the following components must be checked - regardless of whether or not the axles were already checked:

- Check steering and steering linkages using steering wheel angle for problem-free function, visual inspection for bends or cracks.
- Check suspension, all suspension parts such as control arm, suspension struts, steering knuckle, stabilizer bar, subframe, axle beam and their fasteners for bends or cracks.
- Check rims and tires for damage, run-out and imbalance.
 Check tires for cuts in the tread and the sides and check the tire pressure.
- Check mounts for engine, transmission, axles and exhaust system for damage.
- Finally, a proper road test after repairs ensures that the vehicle is safe to drive and can be handed over to the customer.

7.2 Weld Seams and Cast Joints, Check-ing

The color penetration process is used to test for surface cracks. Use the approved repair materials for this.




Note

po Do not brush the area to be checked before the test; otherwise, the reacks will be smeared ation in this document. Copyright by AUDI AG.


7.3 Load Paths



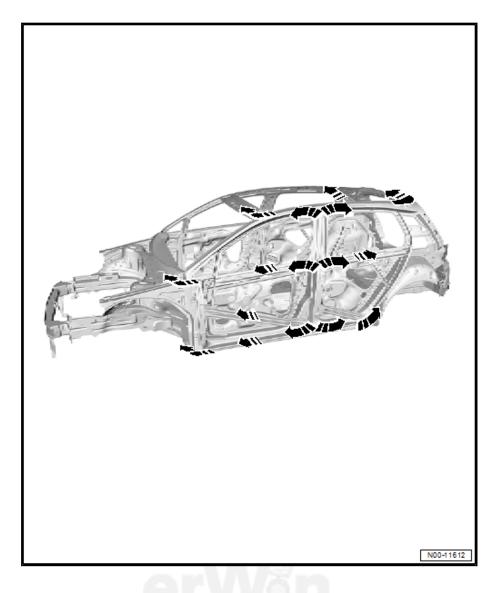

The image above illustrates how the energy is transferred around the passenger compartment during a side impact. When evaluating the damage, particular attention should be paid to the door side impact protection, as well as the A- and B-pillar connection to the sill and roof frame.



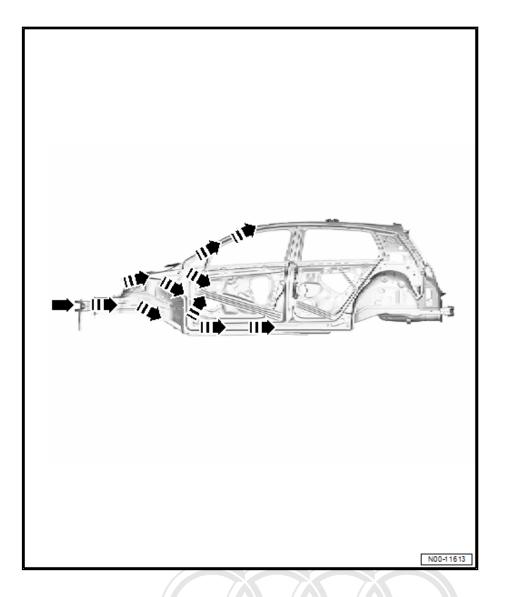

The goal of the body design is for the front of the vehicle body to absorb as much of the energy as possible.


If there is heavy damage to the front of the vehicle structure, the A-pillar transition area to the roof frame or sill must also be closely inspected during the damage evaluation.

Due to the structure, the entire outer shell should also be inspected, since elastic deformations in the high-rigidity structure may cause plastic deformations in the outer shell.

> $\label{protected} \mbox{Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not}$ permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





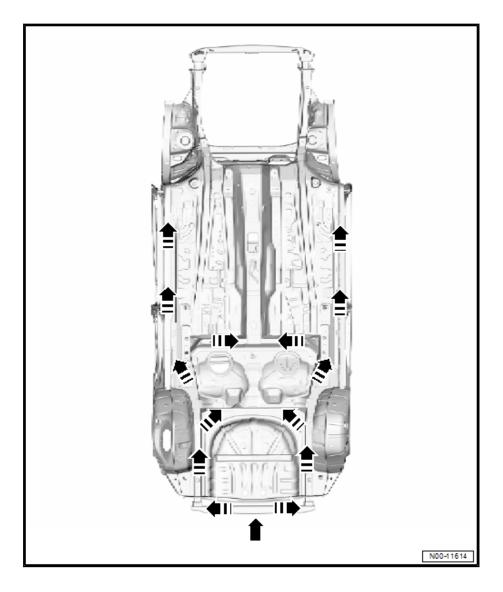


When evaluating damage in the rear, carefully inspect to see if there is any metal distortion in the luggage compartment floor area. Due to the spring effect of the materials used, there may be damage, even though the longitudinal members do not indicate any deviation in discourse. cate any deviation in dimension.

7.4 Measuring / Damage Diagnosis

- Information on approved measuring devices can be found in the Electronic Parts Catalog (ETKA).
- For information on body and gap dimensions, refer to the vehicle-specific repair manual.
- ⇒ Body Repair; Rep. Gr. Body; 00; Technical Data

Telescoping Gauge





Protected by copyright. Copying for private or commercial purposes, in part or permitted unless authorised by AUDI AG. AUDI AG does not guarantee or acc with respect to the correctness of information in this document. Copyright by AUDI AG



To quickly diagnose accident damage, it is often sufficient to perform a diagonal comparison measurement using a telescoping gauge.

7.5 **Overview of Materials Used**

- ⇒ N7.5.1 otes for Deep-Drawn Steel", page 23
- ⇒ N7.5.2 otes for High-Strength and Ultra-High-Strength Steel", page 23
- ⇒ N7.5.3 otes for Aluminum", page 24
- ⇒ C7.5.4 orrosion", page 25
- ⇒ N7.5.5 otes for Carbon Fiber-Reinforced Polymer (CFRP)", <u>page 25</u>
- ⇒ P7.5.6 lastic Characteristics", page 28

7.5.1 Important Notes for Deep-Drawn Steel

Body and floor assembly in series production are produced predominantly from cold-formed deep-drawing sheet metal. For this reason, reshaping accident damage should be carried out in the same way. If the size of the damage does not allow it to be reshaped against the direction of damage, the damaged part must be removed after straightening the connecting surfaces.

7.5.2 Important Notes for High-Strength and **Ultra-High-Strength Steel**

High-strength steel panels are being used increasingly in our vehicles. You can see the areas where these panels are used in an image in the body repair manual.

What are high-strength panels?

Optically normal panels, but they have a higher yield point than normal body panels because of various alloys. This means, with the same force applied to the panel, the dent in the highstrength panel is not as deep as that in a normal body panel.

What must be observed when removing dents?

Dents are removed with standard tools. Due to the higher dent resistance, there is greater rebound so that it may be necessary to expend more force. When buckled areas are reshaped, breaks in the material may occur.

What must be observed when straightening with a bench-type straightening system or hydraulic press?

Due to the greater rebound characteristics of high-strength panels, it must be stretched more than a normal panel before it remains in the desired position. Due to the higher application of force, normal panels that are welded with high-strength panels are strained more. In order to prevent normal panels from yielding or tearing, an additional anchorage must be provided.



Note

- ♦ If a high-strength panel is stretched too much, it suddenly springs back a lot unintentionally!
- For safety reasons, high-strength body panels must not be heated when reforming as with normal body panels!
- Welding high-strength steel according to the repair manual with the specified separation cuts and welding procedures is permitted.

What are ultra-high-strength hot-formed steel panels?

They are steel panels that, as their name suggests, are formed in a warm condition at temperatures between 900 °C and 950 °C. The steel panels gain their high strength through a specific cooling process in the reshaping tool. They are form hardened. The vehicle weight can be reduced without losing strength by using ultra-high-strength hot-formed steel panels. On vehicles with ultra-high-strength hot-formed steel, spot welding devices with inverter technology (see workshop equipment and special tools catalog) are to be used.

Yield points of steel panels used:

Description	Yield points
Normal steel panel	< 160 MPa (N/mm²)
High-strength steel panel	< 220 MPa (N/mm²)
Extra-high-strength steel panel	< 420 MPa (N/mm²)
Ultra-high-strength steel panel	< 1000 MPa (N/mm²)
Ultra-high-strength hot-formed steel panel	< 1000 MPa (N/mm²)

7.5.3 Important Notes for Aluminum

Aluminum is largely used in modern vehicle bodies to reduce weight and to increase, bodygstiffnessor private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability In vehicle construction at distinction as made; between current. Copyright by AUDI AG.

- ◆ Aluminum sheet metal
- Aluminum extrusion profiles (may not be reformed)
- Aluminum cast parts (may not be reformed)

The properties of these components are fundamentally different. If there is damage, pay attention to the vehicle-specific repair manuals.



Note

- The following instructions only apply to conventional steel vehicles on which aluminum metal parts are installed.
- You can see the areas where these panels are used in an image in the respective body repair manual.



Note

- ♦ Use tools for either steel or aluminum.
- ♦ Recommendation: special aluminum tool kit in tool cart

7.5.4 Contact Corrosion

Contact corrosion may occur if unsuitable connecting elements (bolts, nuts, washers and etc.) are used. For this reason, only fasteners with a special surface coating may be installed. In addition, rubber and plastic parts and adhesive are made of non-conductive materials. If there is any doubt as to whether parts should be reused, always install new parts.



Note

- Only use original replacement parts. They have been checked and are compatible with aluminum.
- ♦ Accessories must be approved by Volkswagen AG.
- ♦ If unapproved materials are used, contact corrosion damage is not covered under warranty.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

7.5.5 Important Notes for Carbon^t Fiber=Rein-formation in this document. Copyright by AUDI AG. forced Polymer (CFRP)



Note


Work on the carbon fiber reinforced polymer (CFRP) areas should only be done by qualified personal.

Occupational Safety

When working on CFRP components make sure there is enough protective equipment.

Evacuation must be used. Acceleration of work by raising the parameters can pose a health risk, when vapors, smoke or dust result.

Personal protective equipment must be used.

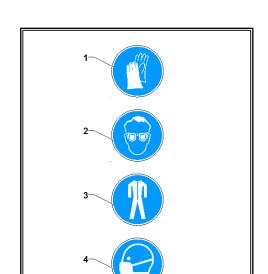

- 1 Safety Gloves
- 2 Protective Eyewear
- 3 Protective Apron
- 4 Mask



Note

- Only specially qualified individuals may perform procedures that handle carbon fiber-reinforced polymer (CFRP).
- Drilling, sawing, grinding, cutting or any other machining procedures are not permitted on carbon fiber-reinforced polymer (CFRP) components.
- Carbon fiber-reinforced polymer (CFRP) is electrically conductive. However it is not permitted to establish a ground connection through carbon fiber-reinforced polymer (CFRP).
- When working on current-carrying wires, every contact with carbon fiber-reinforced polymer (CFRP) components must be disabled (risk of short circuit).
- When repairing the vehicle and during removal and installation of assemblies for example, every hard contact with carbon fiber-reinforced polymer (CFRP) components must be avoided (risk of invisible damage to the carbon fiber-reinforced polymer (CFRP) structure).
- When working on the body, only materials approved by the manufacturer may be used, such as primer, adhesive/and ight. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability rivets. with respect to the correctness of information in this document. Copyright by AUDI AG.
- When working on the body, only procedures approved by the manufacturer may be implemented.

Carbon fiber-reinforced polymer (CFRP) properties:

CFRP is an abbreviation for carbon fiber-reinforced polymer.

Fiber diameter = approximately 6µm

Specific weight = 1.8g/cm³

Tensile strength = 3530 — 4560 Mpa

Elongation = 1.1 — 1.5 %

Between 1,000 and 24,000 individual fibers are combined into bundles for weaving.

Advantages of carbon fiber-reinforced polymer (CFRP) components

- Extremely light: approximately 60% weight saving as compared to steel, approximately 30% as compared to aluminum.
- Highest stability: approximately four times stronger than aluminum.
- ♦ 100 % corrosion-resistant.
- Gas- and pressure-tight.
- High long-term heat resistance.
- Hardly measurable thermal expansion

Disadvantages of carbon fiber-reinforced polymery (CFRP) com-for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

- Very expensive material.
- Difficulty evaluating material if damaged. Damage, such as cracks that are not visible to the human eye, require the use of thermal imaging, infrared and X-ray procedures.
- Repairing structure-relevant carbon fiber-reinforced polymer (CFRP) components is generally not permitted; components must be replaced.

Special notes on using carbon fiber reinforced polymer (CFRP) in production vehicles:

When used in vehicles, the properties must be carefully considered with regard to widespread maintenance servicing by workshops. CFRP components forgive damage less than metal. If a component is damaged it must be replaced. To prevent damage to the remaining components in the vehicle, do not use force or large amounts of strength. Use the specified tools. Pay close attention to the procedure and parameters, as they ensure damage-free work. Patience and care for this work is of the utmost importance.

Not all carbon fiber-reinforced polymer (CFRP) is the same.

Unlike metals the characteristics of CFRP material are not generally visible. The characteristics are example specific. Depending on the resin, fibers, fiber direction and many other factors the components behavior is independent.

Deformation behavior

CFRP components can be constructed so that they displace energy. As a result, they burst or they secure the safety cell during a collision. They can be deigned to be deformable from the construction. It is very important to pay attention to and follow the instructions for each component.

Elasticity after application of force

A CFRP component can be deformed through the load, show breaks or inner damage. After removal of the load a spring back is possible. If this is the case an evaluation of the component is very critical, when this has to do with inner components.

Detecting damage


Cracks, scratches and fiber breakage can be assessed from the outside. When the rear side is visible, impact damage can be partly determined. A delamination (layer separation) that may have occurred through an impact reduces the component strength, the bending strength and thus the breaking and com-

ponent rigidity of the laminate. Because it is not possible to evaluate the damage of CFRP components based solely on a visual inspection and the properties of the components can be drastically worsened by slight damage, it is extremely important to conduct a careful inspection before a damage diagnosis is made.

Overview of nondestructive inspection methods

- Radiography = computed tomography (CT)
- Acoustic = ultrasound, knock test
- Visual = shearography
- Thermal = thermography
- Electrical / magnetic = eddy current testing

Audi AG uses the ultrasonic method for diagnosing carbon fiber-reinforced polymer (CFRP) components.

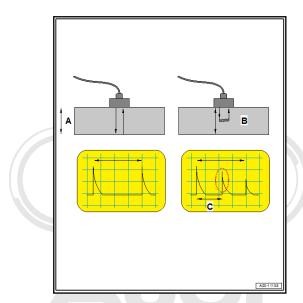

Test sends ultrasonic sound pulses with a very short duration (1-10 µs) that pass through the test component. The sound pulses are reflected by the rear wall and return to the test projected by copyright. Copying for private or commercial purposes, in part or in whole, is not pulses are reflected by the rear wall and return to the test projected by a AUDI AG. AUDI AG does not guarantee or accept any liability as an echo. Compare the data with the data of a malfunction with respect to the correctness of information in this document. Copyright by AUDI AG. free part

- A Material thickness
- B Error in component
- C Error depth

7.5.6 **General Plastic Characteristics**

The areas where plastics are used are very diverse. Property and repair information can be found in the vehicle-specific repair manual, or in the chapter: ⇒ R15 epair", page 71.

7.6 Passive Safety Systems

- ⇒ S7.6.1 ystems (Seat Belt Systems)", page 29
- ⇒ T7.6.2 ensioners, Safety Precautions", page 29
- ⇒ o7.6.3 n Vehicles With Belt Tensioners", page 30
- ⇒ o7.6.4 f Undeployed Pyrotechnic Components", page 30
- ⇒ S7.6.5 ystems (Airbag Systems)", page 31
- ⇒ N7.6.6 otes when Working on Seats with Side Airbag", page 31
- ⇒ f7.6.7 or Disposal", page 31

7.6.1 Restraint Systems (Seat Belt Systems)

Check points:

- Check the seat belt webbing. Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Seat Belt Webbing, Checking.
- Check the belt retractor (locking function). Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Automatic Belt Retractor (Locking Function), Checking.
- Visually inspect the seat belt latch. Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Seat Belt Latch, Visually Inspecting.
- Check the function of the seat belt latch. Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Seat Belt Latch, Checking Function.
- Check the seat belt relays and the belt tongue. Refer to
 ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Seat Belt Relays and Belt Tongue, Checking.
- Check the fasteners and mounting points. Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Fasteners and Mounting Points, Checking after Collision.



Note

If customer refuses to have a damaged seat belt replaced, appropriate note should be made.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

7.6.2 Belt Tensioners; Safety: Precautions ocument. Copyright by AUDI AG.

- Testing, assembly, and repair work may only be performed by qualified personnel.
- The pyrotechnic propellant has no expiration date, this means it has an unlimited service life and is maintenancefree.
- Belt tensioner components may not be opened or repaired; always use new parts.
- Belt tensioner units which have fallen to the ground must no longer be installed in the vehicle.
- Belt tensioner units that are mechanically damaged (dents, cracks) must always be replaced.
- Belt tensioner units should be installed immediately after removing them from the shipping package.
- The belt tensioner unit is to be returned to shipping package when work is interrupted.

- It is not permitted to leave the belt tensioner unit unattended.
- The belt tensioner unit may not be treated with lubricant, cleaning agents, or similar materials, and may not be exposed, even briefly, to temperatures above 100 °C.

7.6.3 Working on Vehicles With Belt Tensioners



Note

Before beginning separation work, straightening work and/or dent removal, remove mechanically activating belt tensioners without load detection (release lock). With electrically activating belt tensioners, the battery ground cable must be disconnected.



Note

If the belt webbing is completely unrolled, the load detection (release lock) hinders the release of the mechanically activated belt tensioner in an accident.



Note

- With belt tensioners with load detection, the belt webbing must not be pulled out when performing separation work nercial purposes, in part or in whole, is not straightening work and/or mental purposes and part of the straightening work and/or mental purposes. The straightening work and/or mental purposes and are generated by separating work, straightening work or dent removal, the belt tensioners with load detection must be removed.
- Information can be found in the vehicle-specific repair manuals. Refer to ⇒ Body Interior; Rep. Gr. 69; Passenger Protection; Seat Belts.

7.6.4 Disposal of Undeployed Pyrotechnic Components

- Airbags,
- Seat belts.
- Pyrotechnic battery cut-out elements
- Active front lid release unit

These must be returned in their original packaging for proper recycling/disposal in accordance with national regulations. If there are any questions, contact the distributor or importer.



Note

Pyrotechnic components deployed in an actual accident can be disposed of as industrial waste.



Note

- This does not apply to seat belt tensioner that function according to the "Wankel tensioner principle".
- These should be handled like undeployed pyrotechnic components, because they cannot be checked using service equipment if all pyrotechnic materials have deployed.

7.6.5 Restraint Systems (Airbag Systems)

Refer to the vehicle-specific repair manuals for all procedures on the airbag systems. Refer to ⇒ Body Interior; Rep. Gr. 69; Airbag System; Component Location Overview - Airbag System as well as the corresponding safety precautions in ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Safety Precautions when Working on Pyrotechnic Components.



Note

- The battery ground cable must be disconnected when working on the airbag system or when performing alignment work during body repairs.
- ♦ Switch off ignition before connecting battery!
- There should not be any people inside the vehicle when connecting the battery!
- Airbag components must not be exposed to temperatures over 100 °C, even if for a short period of time.
- Airbag components must not come in contact with grease, cleaning materials, oil, or similar substances.
- Mechanically damaged airbag components must be reart or in whole, is not placed. permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.
- Wash hands after touching deployed airbag units.

7.6.6 Important Notes when Working on Seats with Side Airbag



Note

- The safety precautions must always be followed when removing the seats.
- ◆ Follow the safety precautions from the vehicle-specific repair manual. Refer to ⇒ Body Interior; Rep. Gr. 00; Safety Precautions; Additional Safety Precautions for Side Airbags.

7.6.7 Instructions for Disposal

Refer to ⇒ Body Interior; Rep. Gr. 00; Safety precautions; Storage, Transport, and Disposal of Airbag, Seat Belt Tensioner, and Battery Cut-Out Units (Pyrotechnic Components).

8 Thermal Joining Techniques

The thermal joining techniques currently used in body repair procedures are presented in the following chapter.

- ⇒ S8.1 pot Welding", page 32
- ⇒ P8.2 lug Welding", page 33
- ⇒ A8.3 rc Continuous and Stitch Weld Seams", page 34
- ⇒ S8.4 oldering", page 34

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG

- ⇒ W8.5 elding", page 35
- ⇒ W8.6 elds", page 36
- ⇒ S8.7 oldering", page 37
- ⇒ J8.8 oining Procedures in Repair (Steel)", page 37
- ⇒ J8.9 oining Procedures in Repair (Aluminum)", page 37

8.1 Resistance Spot Welding

The basic principle for repair welding is to re-create as much of the original welded connection as possible.

This requires that:

- The panels to be welded overlap.
- Both sides of the weld point are accessible to the electrodes.
- The resistance spot welder is strong enough to produce weld spot diameters like at the factory.

During body repair work, access to weld points varies. Therefore, each resistance spot welder must have a complete set of the most common types of electrodes.

Zinc-Coated Panels, Straight-Line Welding

When performing resistance spot welding on zinc-coated panels, observe following points:

- The flanges to be spot welded must touch. If necessary, tension the flanges with pliers.
- This is especially important with high-strength panels because the electrode strength is not great enough.
- Do not weld directly by the clamping pliers with the welding tongs because a large amount of the welding current flows through here due to shunting.
- With small spot weld spacing, weld points in a sequential order or weld every third point to secure, then finish welding. This minimizes the shunting influence.
- Observe Owner's Manual and adjustment notes from manufacturer.


Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

Test Button Weld





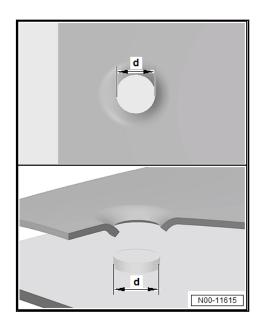

- For the necessary button weld diameter, determine the panel pairing based on the manufacturer's specifications and check with test panels. e or commercial purposes, in part or in whole, is not
- permit Checks all spot weld connections 100% with a chiselytest

Qualitatively acceptable spot welds do not tear into the contact surface, but rather "unbutton".

Calculate the button weld diameter with the following formula and check on test panels before beginning repair.

Square root of T1*3,5*1,15



Note

T1 is the thinnest panel in a panel combination, for example, panel combination of 1.5 mm and 0.8 mm. Example calculation: root of 0.8 x 3.5 x 1.15 = 3.6 mm button weld diameter. With the test, the small welded test strip is rolled or pulled from the second test strip with force perpendicular to the panel surface.

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.


8.2 Gas-Shielded Plug Welding

Gas-shielded plug welding is mostly used when the standard implemented resistance spots cannot be recreated, for example due to limited accessibility.

Always refer to the vehicle-specific repair manuals for this.

General Information regarding Gas-Shielded Plug Welding



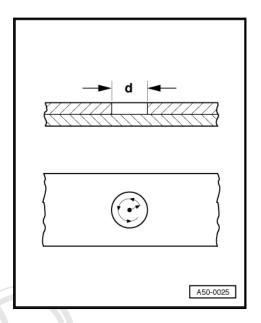

- Loosen weld spots with spot weld cutter or sand off.
- Remove the damaged part, separate with a chisel if necessary.
- Sand down projections.
- Adapt the new part.
- Drill the top panel for plug welding (refer to the vehicle-specific repair manual for the drill bit diameter).
- Clean the flanges and remove the oxide coating.
- Perform plug welding from center, outwarding for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



Riveting are also permitted, to some extent. Observe the body repair repair manual.

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

Gas-Shielded Arc Continuous and 8.3 Stitch Weld Seams

Gas-shielded arc continuous and stitch weld seams are primarily used when joining butt-welded or overlapping separating points. Due to the very high welding temperatures and the altered material properties associated with it, there is increasingly limited use of this joining process. Always refer to the vehiclespecific repair manuals for this.

The weld seams may not be sanded otherwise the strength of the weld seam will be impaired.

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

8.4 MIG Soldering

MIG soldering primarily differs from the gas-shielded arc stitch or continuous weld seam in that it requires significantly lower

temperatures. The advantage of MIG soldering is a significant reduction in material distortion in the components being connected. The joining process is also suitable for larger flat components.

Other advantages include:

- Minimal structural changes in the components.
- Minimal damage to the corrosion protection applied during production.
- Preserves the zinc coating on the components.

What is MIG soldering? (not approved for AUDI AG vehicles)

- Brazing procedures are also called gas-shielded metal soldering.
- The base material (body panel) is not melted on; the solder coats the flanks and connects the components.
- MIG stands for metal inert gas. The inert gases are not actively involved in the processes between the electric arc and welding filler material.
- Argon or helium are among the inert gases to be used, and are mixed with carbon dioxide or oxygen.
- Up to 450 °C (842 °F): solder
- ♦ Above 450°C (842 °F): braze

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

8.5 Aluminum Welding

Metal Inert Gas (MIG) welding is used by the manufacturer and in service.

Argon is used as inert gas.

- Before welding, remove any underbody protection and paint from the components.
- Then remove the approximately 40 mm of the oxide layer on both sides using a stainless steel brush.
- To avoid formation of cracks, weld seams must be drawn around section corners.



Note


- Use the Panel -4D0 898 103- for welding practice and repairs.
- Additional information can be found in the "aluminum welding" training guide.

Same Material, Underlying

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





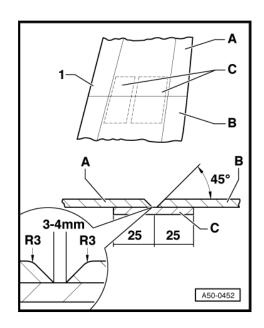

Same material -C- is created from remainder of new -B- or old parts -A-. Same material should also be underlaid on beaded panel edges. On small cross sections or large panel edges, the same material is separated.

Bevel both panels 45°. Round outer edge (radius = 3) and chamfer inner edge.

Panel tips must be 3 to 4 mm apart.

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

Laser Welds 8.6




Note

This joining procedure is only used during manufacture.

Information on the replacement procedures can be found in the following chapter overviews. Refer to ⇒ J8.8 oining Procedures in Repair (Steel)", page 37 or ⇒ J8.9 oining Procedures in Repair (Aluminum)", page 37.

> Protected by copyright. Copying for private or permitted unless authorised by AUDI AG. AU with respect to the correctness of informat



Always refer to the vehicle-specific repair manuals for this.

In laser welding, a high-energy light beam is directed onto the weld point via optical lenses or fiber optics. During the welding process, the upper panel is melted through and as well as with the lower panel on the surface, thereby forming a weld without using any additional materials.

8.7 **Laser Soldering**



Note

This joining procedure is only used during manufacture.

Information on the replacement procedures can be found in the following chapter overviews. Refer to ⇒ J8.8 oining Procedures in Repair (Steel)", page 37 or ⇒ J8.9 oining Procedures in Repair (Aluminum)", page 37

Always refer to the vehicle-specific repair manuals for this.

Generally, an additional material is used during laser soldering. The soldered connection is not fundamentally different than that of an MIG soldered connection.

Only the fusing of additional material does not occur using electric arc, but rather using a concentrated light beam the same as for laser welding. Due to the laser technology, the energy can be applied at a precise point. Undesirable side effects, such as heat distortion, are negligible.

8.8 Replacement Joining Procedures in Repair (Steel)

In production	In repair
Spot welds	Spot weld bonding / MAG plug welding / MAG welding
MAG Welding	MAG Welding
MIG Soldering	MAG Welding
Laser Welds	MAG Welding Protected by convright, Copying for private or commercial purposes, in part or in whole, is not
Laser Soldering	MIG soldering (not approved for AUD) es not guarantee or accept any liability AG vehicles) to the correctness of information in this document. Copyright by AUDI AG. Bonding MAG welding Note the information in the repair manual
Bonding	Bonding / MAG welding
Spot weld bonding	Bonding with spot welding / additional spot welds / additional MAG welding
Pop rivets	Pop rivets Only use pop rivets specified in the repair manual. Commercially available pop rivets generally do not have sufficient strength.

8.9 Replacement Joining Procedures in Repair (Aluminum)

In production	In repair
MIG welding	MIG welding
Spot welds	Not used
MIG Soldering	Not used
Laser Welds	Bonding and riveting
Bonding	Bonding and riveting
Punch Rivets	Punch Rivets

In production	In repair
Pop rivets	Pop rivets Only use pop rivets specified in the repair manual. Commercially available pop rivets generally do not have sufficient strength.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



9 Body Structural Adhesive D 180 004M2, Application

⇒ S9.1 urfaces, Preparing", page 40

Bonded Joints, Detaching

Body bonded joints can be detached by applying heat. The adhesives used in the vehicle construction and the repair are destroyed at temperatures 180 – 200°C.



Note

- Wear protective gloves and eyewear.
- ♦ Avoid direct contact of the adhesives with the skin. in part or in whole, is not
- ♦ Avoid inhaling solvent vapors: information in this document. Copyright by AUDI AG.
- ♦ Only process adhesives in well-ventilated areas.
- ♦ Always note the hazard information from the manufacturer.
- Also note the accident prevention regulations applicable in the respective country.
- ♦ Note the corresponding safety data sheets for the adhesive.
- ♦ Do not smoke, eat or drink at the work station.
- ♦ Use suitable extraction.
- The vehicle, parts and adhesive materials must be at processing temperature (acclimated). The processing temperature must be kept for 30 min before work on the adhesive surfaces starts.
- The adhesive surfaces must be free of oils, adhesive residue, humidity, paint and oxide coatings.
- Body structural adhesive must only be used on bare metal components.
- Only use sanding material based on silicon carbide (SIC) for grinding down the adhesive surface.
- Pay attention that the cleaned surfaces are only touched with clean gloves in order to avoid transferring hand sweat or contamination to the adhesive surface.
- Merging must happen immediately after applying the adhesive, in order to ensure a high-quality and secure bonding.
 Otherwise the adhesive bead must be removed and the surface treatment and application of the adhesive must be repeated.
- Carefully prime the accessible adhesion areas after hardening and seal them with body sealant. Protect adhesion areas in cavities against corrosion using cavity sealant.





Note

- ♦ Use the adhesive material within the processing time. Within this time frame the adhesive material must be applied and connected to the body component. Any resistance weld spots or mechanical joining processes (for example rivets and bolts) in the area of the adhesive must be performed within this time frame.
- ♦ Do not stress bonded parts until hardened.



Note

During colder seasons, over night or in countries with a cold climate, suitable measures must be taken to reach the minimum hardening temperature.

- Optimize the controls of the heating system, for example deactivate reducing temperatures at night.
- Keep doors and windows closed, and prevent drafts.
- Install auxiliary heaters in the area of the body repair.
- In addition to these guidelines, mind the respective procedure descriptions for body repairs!

9.1 Adhesive Surfaces, Preparing

Pre cleaning

Remove solid layers like dirt, rust, paint coats (CDC).

Cleaning


 To prevent spreading possible grease residue when grinding down afterwards, clean the adhesive surfaces with a lint-free cloth, soaked with isopropyl alcohol or acetone. Allow the cleaned surfaces to ventilate for 15 minutes.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.






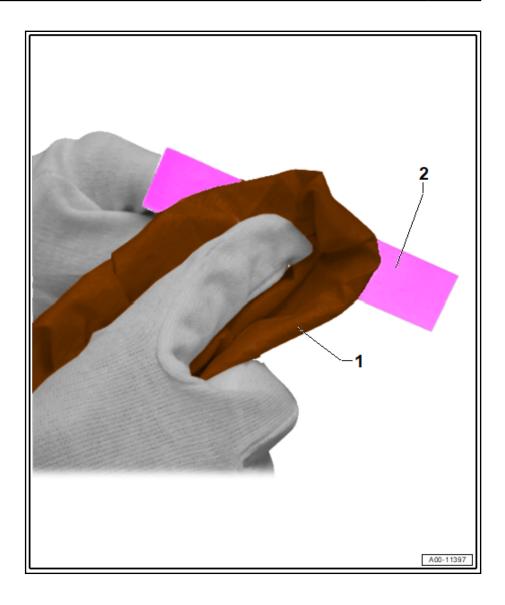

Grinding down

To improve adhesion, grind down the adhesive surfaces with grid 150 to 180 sandpaper. Use crossover griding process.



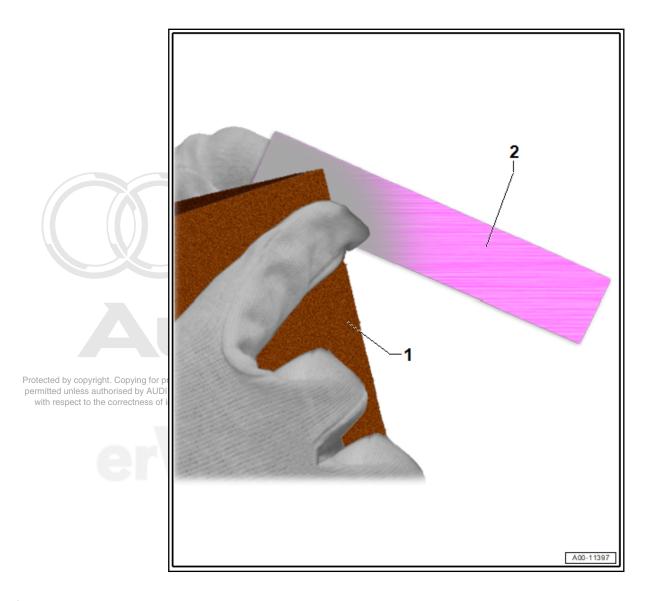


Cleaning



Note

After the last cleaning procedure the adhesive must be applied within four hours, to prevent contamination as well as the formation of an oxide coating on the aluminum material. Repeat the preparations after four hours without application of the adhesive.

- Afterward clean the bare metal adhesive flange areas with a lint-free cloth, soaked with isopropyl alcohol or acetone, until no residue is visible on the cloth.
- Allow the cleaned surfaces to ventilate for 15 minutes, the adhesive surfaces must be completely dry.

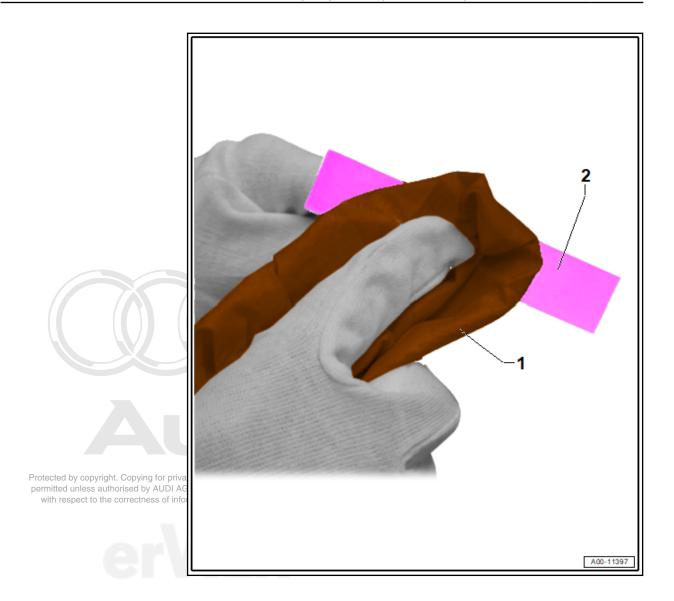

Processing conditions

The ambient and material temperature when processing, must be at least "minimum temperature 15 $^{\circ}\text{C}$ " and a most "maximum temperature 35 $^{\circ}\text{C}$ ".

Higher processing temperatures reduce the processing time.

Processing time at 15 ° C (59 °F) 80 min

Processing time at 18 ° C (64.4 °F) 75 min

Processing time at 20 ° C (68 °F) 65 min

Processing time at 23 ° C (73.4 °F) 60 min

Processing time at 25 ° C (77 °F) 50 min

Processing time at 30 ° C (86 °F) 40 min

Processing time at 35 ° C (95 °F) 30 min



9.1.1 Joining Process



Note

- ♦ If the adhesive escapes on both sides along the entire length of the joining area, too much was applied.
- ♦ 1 cartridge with 195 ml is enough for approximately 5 meters of flange.

Adhesive cartridges must be used with plunger adhesive guns.


Tools

Prepare the Cartridge Gun -VAG1628- or -

 $Pneumatic \ _{y}Gun \ _{ight} 18_{o}Bar \ _{ro}V \ _{A}S6648 \ _{mi} or \ _{ro} \ _{al} \ purposes, in part or in whole, is not \ _{s} \ _{s$

Pneumatic Cartridge Gun VAG1761/1s for seam sealing up AG.

- 1 Press out the adhesive without mixing tube, until both components exit the cartridge.
- 2 Attach the mixing tube to the cartridge and check the exiting adhesive.

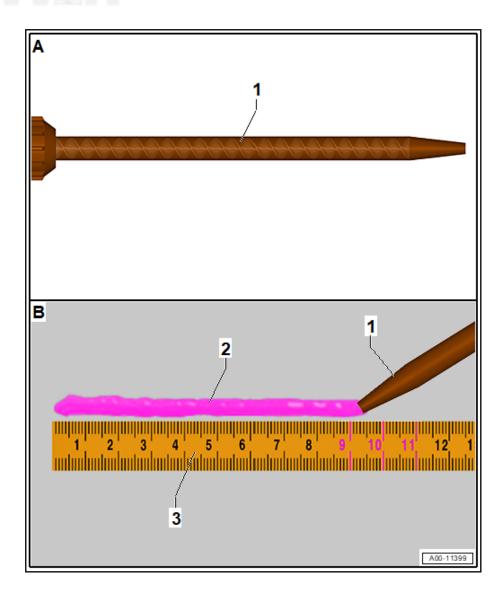




- $\bf 3$ Pay attention that both components evenly mix in the mixing tube.
- 4 Before application to the joining area, apply a 10 to 20 cm bead on a paper towel or similar and throw away later on. The hardening process can also be checked with this bead.
- 5 In addition, apply an approximately 10 cm long sample adhesive bead on a paper towel or similar.


Apply the adhesive.

Applying adhesive on both joining area flanges.

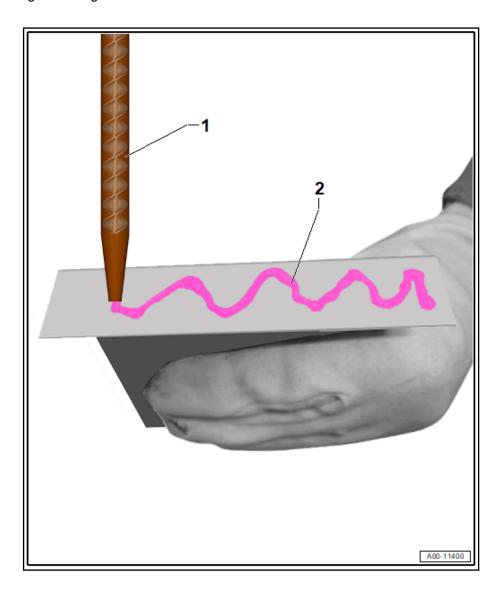

Spreading the adhesive flat on both joining area flanges with clean tools. Application height 0.5 mm



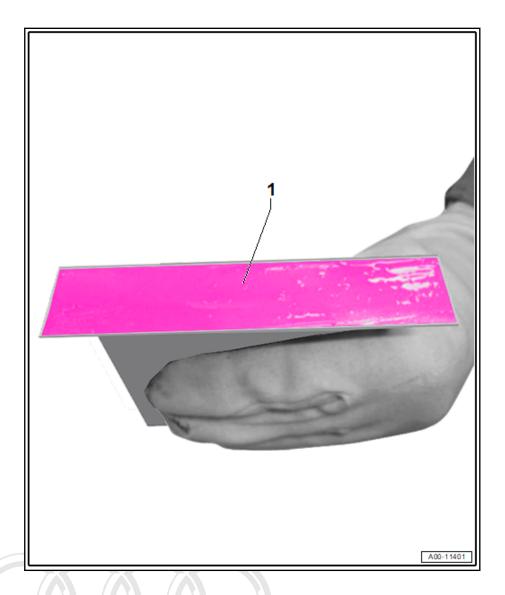


- Locations uncoated with cataphoretic dip coating (CDC), or bare metal locations in cavities must be painted or filled with structural adhesive.
- Apply an additional adhesive bead to the center of the joining area.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



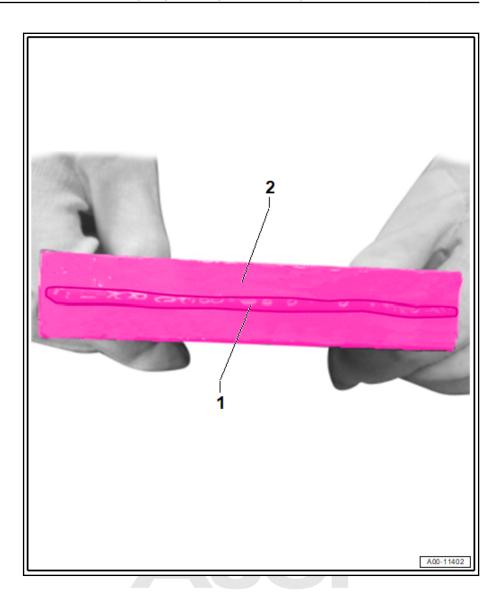


Connect the parts.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





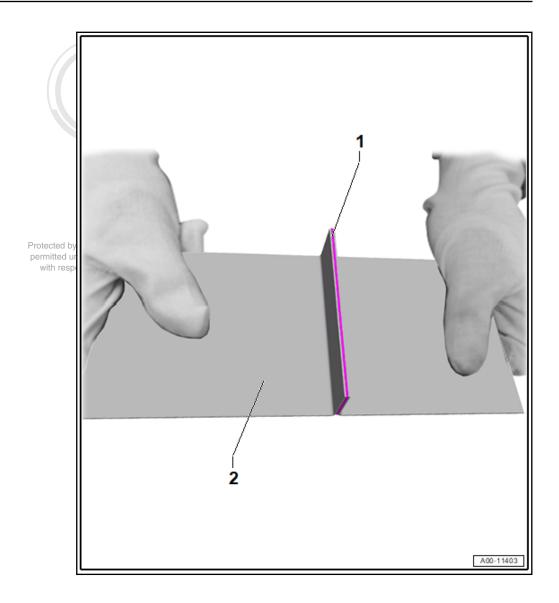


Connecting the parts



Note

- The connection must happen immediately after applying the adhesive, in order to ensure a high-quality and secure bond-
- Otherwise the adhesive bead must be removed and the surface treatment and application of the adhesive must be repeated.
- The layer thickness of the adhesive after bonding must not exceed 1 mm.
- Remove excess adhesive.



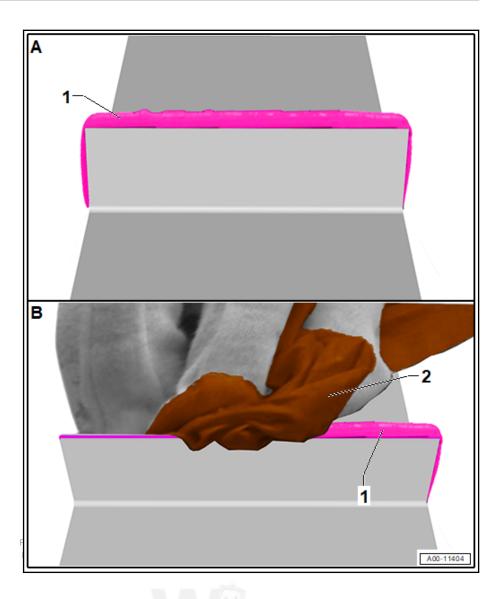

Remove excess material with a clean towel.

Clean visible surfaces with a clean towel soaked in acetone.

Hardened material can only be removed mechanically.

9.1.2 Hardening

The body structural adhesive used hardens at temperatures between a minimum of 18 °C (64.4 °F) and a maximum of 80 °C.(176 °F)

The hardening process can be sped up by heat (for example an infrared heater or in a paint booth).

Infrared heaters only heat up sections of the body and are thus only suitable for small repairs.

Only use devices with a temperature setting, automatic distance measuring and visualization of the measuring point.

Do not stress bonded parts until assembling stability is reached.



9.1.3 Assembling Stability



Note

- ♦ The temperature of the object must be above the minimum temperature for hardening for the entire time.
- If the minimum temperature for hardening has not been kept for the specified time, the waiting period must be prolonged or additional heat must be applied to the adhesive bond.
- If the minimum temperature for hardening falls below significantly, this can lead to irreversible damages in the bonded joint. This has a negative effect on the strength of the bonded joint.



Note

After the assembly stability has been reached the vehicle can be lifted off the alignment system. Assembly work can be performed.

Protected

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

 Moving and further processing at the vehicle after repair bonding is only allowed after a minimum curing time of 12 h at 23 °C (73.4 °F).

The waiting period can be reduced by applying heat. For example, curing time at 60 °C (140 °F) 60 min.



Note

- ◆ The temperature of the object must be above the minimum temperature for hardening for the entire time.
- If the minimum temperature for hardening has not been kept for the specified time, the waiting period must be prolonged or additional heat must be applied to the adhesive bond.
- If the minimum temperature for hardening falls below significantly, this can lead to irreversible damages in the bonded joint. This has a negative effect on the strength of the bonded joint.

After this time the vehicle meets the crash requirements and may be moved under traffic laws.

The vehicle can be handed over to the customer.

The time frame from connecting the repaired parts until operation must be a minimum of 96 h at 18 $^{\circ}$ C (64.4 $^{\circ}$ F).

9.1.4 Corrosion Protection

Carefully prime the accessible adhesion areas after hardening and seal them with body sealant.

Protect adhesion areas in cavities against corrosion using cavity sealant.

9.1.5 Work Sample




Note

A work sample can be created to make sure there is a correct bond. The creation of the work sample is described in the processing instructions of the adhesive.

- With a negative result of the working sample (no correct hardening), no correct bonding can be ensured.
- In this case measures must be taken to ensure correct hardening or repeat the adhesion if necessary.

Check and evaluate the hardening of the work sample -1- after reaching assembling stability by breaking the sample -arrow. The adhesive must break and contain no liquid or soft components.

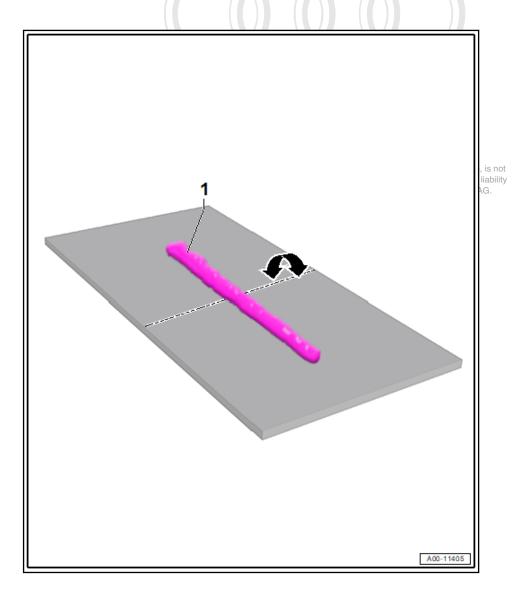

10 **Cold Joining Procedures**

- ⇒ 10.1 , page 52
- ⇒ B10.2 olts", page 59
- ⇒ 10.3 , page 61

10.1 **Rivets**

- ⇒ R10.1.1 ivet", page 52
- ⇒ R10.1.2 ivet", page 53
- ⇒ P10.1.3 roblems", page 55
- ⇒ R10.1.4 ivets", page 58




Note

Please refer to the vehicle-specific repair manuals or the Workshop Equipment Catalog for information on required special tools, testing equipment, and tools.

10.1.1 Solid Rivet


Opening the solid rivet

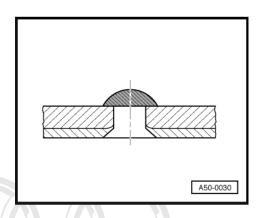

- First make separating cuts, if necessary.
- Sand off closing head and press out the solid rivet with the rivet tool.
- Remove the damaged part, separate with a chisel if necessary.

Solid Rivet, Installing

Protected by copyright. Copying for private permitted unless authorised by AUDI AG with respect to the correctness of infor





- Fit new parts, apply adhesive and place new part on body and secure.
- Stamp the flange with the rivet tool.

When stamping, the punch hole and the imprint are made in one process.




Note

Adjust the rivet tool to material thickness for all procedures. To prevent flange from gaping after stamping, insert staples in the punched holes.

Insert the solid rivet and affix the closing head using the rivet tool.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or acc with respect to the correctness of information in this document. Copyright by



There are corresponding rivet tool inserts for the various rivet diameters.




Note

- Contrary to the series, all rivet connections are also bonded in service. Refer to bonded joint. The solid rivet is made out of aluminum.
- There are different solid rivets available. Refer to the vehicle-specific instructions for this.

10.1.2 Pop Rivet

Opening the pop rivet

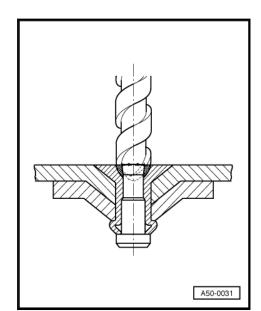


- First make separating cuts, if necessary.
- Drill out the pop rivet, drill bit diameter 4.5 mm.
- Remove the damaged part, separate with a chisel if necessary.



Note

Catch pop rivet remnants. If remnants fall into the cavities and can no longer be removed, they must be worked into the filler wax.

Pop Rivet, Installing

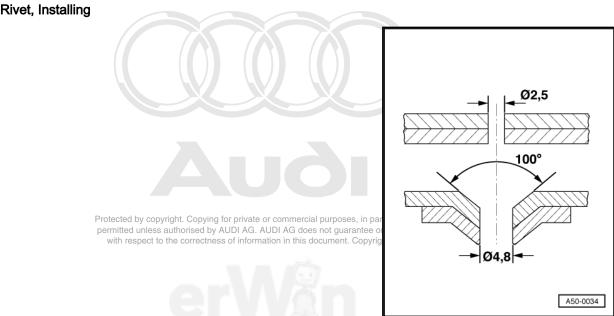


- Fit new parts, place on body and secure.
- Drill old and new part or same material together, 2.5 mm diameter.
- Remove the new parts.
- Imprint drilled holes in all parts with rivet tool.





Note

- Adjust the rivet tool to material thickness for all procedures. The diameter increases to 4.8 mm with imprinting. The imprint must face inward on all parts.
- ♦ Assembly sections cannot be imprinted. Lower the new part with assembly section, remove part and drill out the assembly section to 4.8 mm diameter.
- Apply the adhesive.
- Insert the pop rivet and pull the pin with rivet pliers.

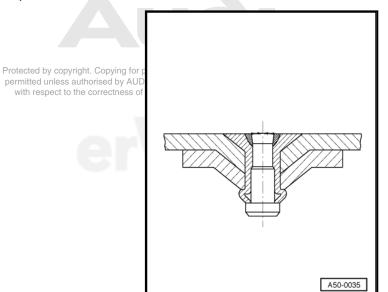




Note

- Contrary to the series, all rivet connections are also bonded in service. Refer to ⇒ S9 tructural Adhesive D 180 004 M2, <u>Application", page 39</u> .
- There are different pop rivets available. Refer to the vehiclespecific instructions for this.

10.1.3 **Rivet Problems**

Open countersinks

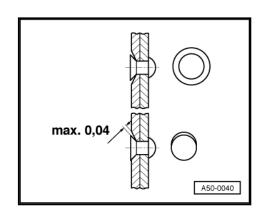




Open countersinks over the entire circumference are not permitted. Partially open countersinks up to a gap width of 0.04 mm are permitted.

Sizing, for example, with a cambered die, is permitted as long as the tolerance for closing and setting head are maintained.

Non-fitting rivet heads

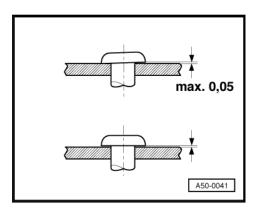


Loose rivets are never permitted.

A partial gap up to 0.05 mm is permitted.

Bulges at the rivet connection




Protected by copyright. Copying for private or commercial purposes, in part or in w permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept with respect to the correctness of information in this document. Copyright by AU



During the riveting process, the rivet material is pushed into the gap and causes bending stress to the rivet.


This type of bulge is not permitted.

Bulges between the rivet connections

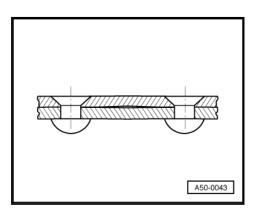


Bulges may not exceed a gap width of 0.3 mm.

Shear cracks

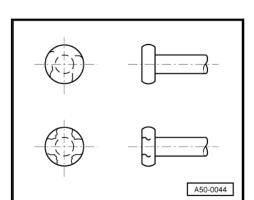


Cracks that do not overlap are permitted (top).

Notches

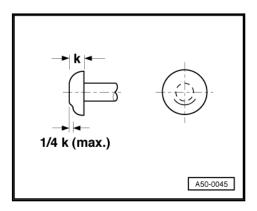

The permitted notch depth is 1/4 * height of the head.

Rings

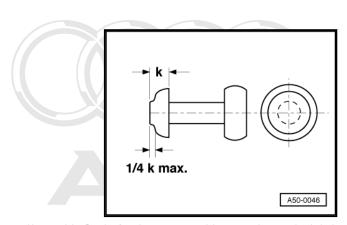


Rings form in the head when a riveting header is used it hat its authorised by AUDI AG. AUDI AG does not guarantee or accept any liability too small.

The permitted depth of the rings is 1/4 * height of the head.

The fully formed ring is not permitted.

Offset closing head



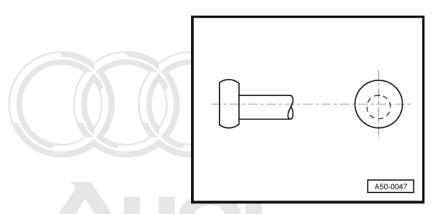

An offset head is not permitted if the head touches the shaft and the rivet hole is visible.


Kerb-Konus Rivets tected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability 10.1.4 Kerb-Konus rivets coated with stainless steel are inserted.



Note

Due to the corrosion risk, stainless steel rivets may not be drilled out or sanded.

Riveting processes

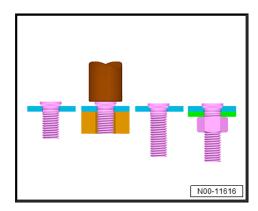

- A Setting the rivet
- B Pressing process
- C Inserting and punching out
- D Finished Kerb-Konus rivet connection

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.


10.2 Flow-Drill Bolts

⇒ D10.2.1 rill Bolt Connection, Producing, Upper Section Pre-Punched", page 59

⇒ D10.2.2 rill Bolt Connection, Producing, Upper Section Not Pre-Punched", page 59

⇒ D10.2.3 rill Bolt Connection, Creating, When Replacing Upper and Lower Section", page 60

When using flow-drill bolts, the lower component is heated by the frictional heat generated by the turning bolt. Then the selftapping screw is screwed into the soft aluminum.

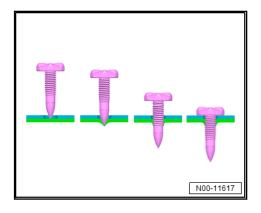

Flow-Drill Bolt Connections, Servicing



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not protected unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

- Flow-drill bolts have been introduced on the Audi R8 that can be replaced using the FD Bolt Socket -VAS852 007A-.
- The repair concept for the pure aluminum body components is the same as the repair procedures used on previous Audi aluminum vehicles.
- Using the tool allows the best use of the threaded connection during repairs.

The production of a flow drill bolt connection is presented in the following based on three examples.

10.2.1 Flow Drill Bolt Connection, Producing, **Upper Section Pre-Punched**

- Loosen the flow drill bolt threaded connection using a socket for flow drill bolts.
- Remove the upper section.
- Clean the adhesion area with cleaning solution.
- Apply two-part epoxy adhesive to the entire area using a pneumatic adhesive gun.
- Position the new part and tighten using the flow drill bolt socket and tighten new bolts to 5 Nm.

10.2.2 Flow Drill Bolt Connection, Producing, **Upper Section Not Pre-Punched**

Loosen the flow drill bolt threaded connection using a socket for flow drill bolts.

- Remove the upper section.
- Insert the hole finder into the existing flow drill bolt threads.
- Position the new part.
- Label the holes in the new part by hitting it lightly with a plastic hammer.



Note

Allow for the flow drill bolt repair set offset: only make a superficial mark if possible.

- Remove the upper section.
- Dill 7 mm diameter holes in the new part.
- Clean the adhesion area with cleaning solution.
- Position the new part and tighten using the flow drill bolt socket and tighten new bolts to 5 Nm.

10.2.3 Flow Drill Bolt Connection, Creating, When Replacing Upper and Lower Section

- Loosen the flow drill bolt threaded connection using a socket for flow drill bolts.
- Remove both sections.
- Using both parts at the same distance as with the original connection, make 4 mm holes. Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not


permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

with respect to the correctness of information in this document. Copyright by AUDI AG.

- Remove the new parts.
- Expand the 4 mm holes in the upper section to 7 mm.
- Clean the adhesion area with cleaning solution.
- Apply two-part epoxy adhesive to the entire area using a pneumatic adhesive gun.
- Position the new part and tighten using the flow drill bolt socket and tighten new bolts to 5 Nm.

Flow Drill Bolt Repair Set

The repair set serves as a means of marking the holes on the new parts where the flow drill bolt threaded connections are used. Using the hole finders, it is possible to transfer the hole positions for the flow drill bolts to the Audi aluminum vehicles if a repair is required. First loosen the old flow drill bolts by using the socket. Then the damaged panel is removed. Now the flow drill bolt repair set is installed in the existing holes in the aluminum panel that was not replaced. Do this using the ring wrench. The new aluminum panel is aligned to the vehicle and attached with crimping pliers. Using light hammer strokes (rubber hammer), the holes from the existing panel will be transferred onto the replacement part with assistance from the flow drill bolt repair set. The replacement part that now contains the marks is removed again. Holes are drilled at the transferred marks. It is then possible to secure the flow drill bolt threaded connections of the new part to the body using the socket





Devices

Only the devices approved in the Workshop Equipment Catalog may be used.


10.3 Clinching

Clinching is a press-joining process to connect sheet metal without using additional materials. One can expect to apply it to joining procedures as well as to reforming procedures, because the connection is attained by reforming the material.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



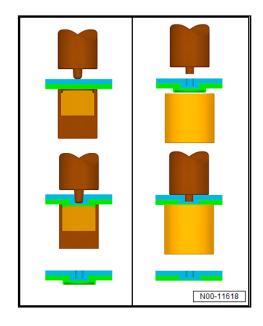

Repair Information

- First make separating cuts, if necessary.
- Remove the old flange by peeling.
- Align the remaining flange.



Note

Adjust the rivet tool to material thickness for all procedures.

- Remove the damaged part, separate with a chisel if necessary.
- Fit new parts, and install solid or pop rivets based on the repair manual "Body Repair".

Devices

Only the devices approved in the Workshop Equipment Catalog may be used.

11 Separation Technologies in Body Repair; Application

- ⇒ 11.1 , page 62
- ⇒ 11.2 , page 62
- ⇒ 11.3 , page 62
- ⇒ 11.4 , page 62

11.1 Drilling

Drilling is used to loosen resistance weld spots and rivets. Make sure no underlying components are damaged while drilling poses, in part or in whole, is not when loosening two or more welded connections, the panel of the copyright by AUDI AG. remaining on the vehicle may not be impaired more than necessary. After drilling, carefully remove any drill shavings from the cavities (vacuum).

11.2 Sawing

The technician will decide between the two established device types for sawing:

- ♦ Short stroke pneumatic saw
- Oscillating saw

Advantages of the short stroke pneumatic saw:

- Faster separation.
- Possible to saw curves.
- Can also be inserted at sharply angled profiles.

Advantages of the oscillating saw:

- Clean, straight cuts.
- Low penetration depth, therefore it is particularly suitable for double-layer panels.



Note

After sawing, carefully remove any saw shavings from the cavities (vacuum).

11.3 Sanding

Sanding can be a very favorable alternative to drilling, especially when loosening high-strength welded connections. Weld points, laser weld connections, or brazed seams can be loosened very efficiently by sanding. Also make sure here that the underlying materials are not impaired or damaged any more than necessary.


Disadvantages of sanding:

- Due to the flying sparks, extensive protective measures are necessary on the vehicle and in the surrounding area.
- Higher temperature build-up than when drilling, thus more damage to residual material and corrosion protection.

11.4 Milling

In body repairs, the technician decides between a ball end nose mill -A- and a BTR mill -B-.

N00-11619

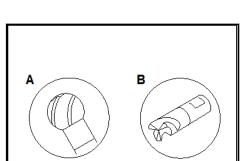

A ball end nose mill is used if the spacial conditions do not allow the BTR mill to be used for loosening weld points.

When working with the BTR mill, it must be made sure that cuts do not tilt into the high-strength steel. They can break easily due to the hardness of the cuts. Therefore, it should always be worked with a suitable tool (not a hand drill).



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



12 Surface Repairs

- ⇒ R12.1 emoval Techniques, Steel Panel", page 64
- ⇒ R12.2 emoval Procedures, Aluminum Panel", page 65
- ⇒ a12.3 nd Aluminum Body Filler, Handling", page 66
- ⇒ T12.4 in, Handling", page 67
- ⇒ A12.5 ccurately Contoured Surface Definition, Transfer to Paint Shop", page 67



Note

Generally, the inner corrosion protection must be paid attention to during all bulge corrections.

12.1 Dent Removal Techniques, Steel Panel

- ⇒ C12.1.1 lassic Dent Removal Procedure, with Paint Damage", page 64
- ⇒ P12.1.2 ressing Bulge Correction Procedure, without Paint Damage", page 64
- ⇒ E12.1.3 xterior Dent Corrections / Pulling Dent Removal Procedure", page 64

12.1.1 "Classic" Dent Removal Procedure, with Paint Damage

The classic dent removal method using a hammer and counterhold is rarely still used on modern vehicle bodies.

The disadvantage of this technique is that usability is limited (depending on construction) as well as the overextension of materials required by this method. The resulting excess of material must often be thermally reduced, which in turn results in consider for private or commercial purposes, in part or in whole, is not erable disadvantages for the material strength lies and project of the confectness of information in this document. Copyright by AUDI AG. protection.


12.1.2 "Pressing" Bulge Correction Procedure, without Paint Damage

This dent removal method that does not cause paint damage is mostly used for minor parking and hail damage. Here the dent is softly pressed outward from the inside. The pressing is done circularly around the center of the dent in multiple stages, so that the paint can also be reshaped without a formation of cracks.

A - Pressing Set Example

12.1.3 "Exterior Dent Corrections / Pulling" Dent Removal Procedure

The exterior dent removal method is used as a bonding technique without damage as well as a method with paint damage, due to pulling aids being attached. This method selection therefore depends on the type of damage. For both procedures, the dent is pulled out of the panel from the outside. The long reshaping process significantly reduces the tension in the material structure. It is also referred to as "soft" or "no-shock" reshaping.

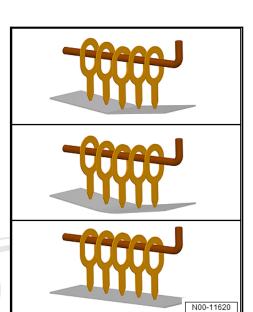

Advantages of these bulge removal methods:

- Overstretching of material is reduced
- Minimal corrosion protection damage.
- Minimal disassembling of the vehicle.
- Maintains the original joint (compared to component replacement). Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not

AUDI AG. AUDI AG does not guarantee or accept any liability 12.2 Dent Removal Procedures, th Aluminum rmation in this document. Copyright by AUDI AG.

Panel



Note

Aluminum parts must be covered when sanding and welding steel parts. Any steel shavings that contact aluminum must be immediately removed or else contact corrosion can occur.



Note

- ♦ Use separate tools for steel or aluminum.
- Recommendation: Aluminum tool kit in the tool cart (refer to Workshop Equipment Catalog)

The dent removal techniques for aluminum components are not fundamentally different than those for steel components. However, due to the different material properties, several points must be noted:

- The risk of material expansion is greater with aluminum than with steel.
- Sharp-edged and hard dent removal tools (for example, steel hammer) should be avoided and should be replaced with plastic, wood or aluminum hammers.
- Flattening procedures on aluminum panels begins, contrary to steel panels, in the center of the dent.
- If the material stretches, this can be corrected by applying heat and retracting.





Note


Do not exceed the maximum heat of 150° C (302 °F) during retraction; otherwise, the component may become damage.



Note

Replace the part if a tear forms when removing dents.

Controlling Temperature When Heating

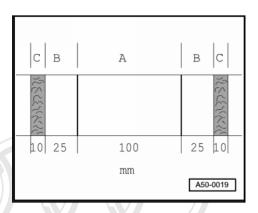

No tempering colors can be recognized when heating aluminum. Therefore, the temperature must be determined using thermo-strips.

Thermo-strips change color at specific temperatures.

- A Warming area
- B Free zone
- C Thermo-strips

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

12.3 Metal and Aluminum Body Filler stan e correctness of information in this document. Copyright by AUDI AG. dling

Using metal and aluminum body filler has many advantages:

- Very good adhesive properties on bare surfaces
- Higher coat strengths are possible than with polyester body filler.
- When handles correctly, there is a low tendency of "shrinking" or "sagging".
- Due to the low application of heat, they can also be used in areas with adhesive.
- No visible marks in the overlapping areas.



Note

Only approved body filler materials may be used.



Note

- Note the handling information on the containers.
- Adhesive residue or similar material must be completely removed from the joints before applying the body filler.
- The surface temperature must be checked when drying with the infrared heater.
- Self-regulating infrared heaters tend to have measurement errors on small surfaces, which can lead to component damage.

12.4 Unleaded Tin, Handling



Note

- ♦ Handling tin, even unleaded tin, is no longer permitted.
- ◆ To create a surface with correct contours, use the materials listed. Refer to ⇒ a12.3 nd Aluminum Body Filler, Handling", page 66.

12.5 "Accurately Contoured Surface" Definition, Transfer to Paint Shop

The contoured surface is a surface with the dimensional accuracy of the edges and seams to the surface.

It is specified when:

- Any surfaces or parts that have been worked on, such as removing dents, welding or spackling, must be dry sanded with minimum P 80 grit sandpaper.
- ◆ The vehicle paint shop technician must then re-create the respective surface in a maximumrofctwoystepsat. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



Note

Only approved body filler materials may be used. Neither unleaded nor leaded alluvial tin is approved for any procedure.



13 Straightening Procedures on Vehicle Structure

- ⇒ 13.1 , page 68
- ⇒ C13.2 uts", page 68
- ⇒ S13.3 ub-Parts and Partial Sections", page 68

13.1 Straightening

Body and floor assembly in series production are produced predominantly from cold-formed deep-drawing sheet metal. For this reason, reshaping accident damage should be carried out in the same way.

If the size of the damage does not allow it to be reshaped against the direction of damage, the damaged part must be removed after straightening the connecting surfaces.

13.2 Separating Cuts

Separating cuts that influence the fatigue strength of the body and the operational safety and road safety of the vehicle must be carried out according to the specifications of the applicable body repair manual.

13.3 Body Sub-Parts and Partial Sections

"Sub-parts" include sections of individual parts (for example, front and rear end points) that are delivered pre-cut from the replacement parts distribution center.

- ♦ In contrast to this, "partial sections" are to be cut out from
 "replacement parts". In individual cases, work is to be performed exactly according to the methods described and repses, in part or in whole, is not
 resented in the body repair manual dby AUDI AG. AUDI AG does not guarantee or accept any liability
- with respect to the correctness of information in this document. Copyright by AUDI AG.

 Because the use of "sub-parts" or "partial sections" as well
 as special resources influence repair times, the special resources are included separately in the repair description.

14 Corrosion Protection

⇒ P14.1 rotection on Attachments and Welded Parts", page 69

⇒ C14.2 avities", page 69

The standard corrosion protection must be reapplied after servicing with the materials specified by the manufacturer.

The corrosion protection used in production is described in the general and vehicle-specific ⇒ Paint Manual.

14.1 Corrosion Protection on Attachments and Welded Parts

- ♦ Prime bare panel surfaces immediately after the repair opying for private or commercial purposes, in part or in whole, is not
- Holes must be deburred.
- permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.
- Always apply welding primer/structure adhesive (according to the repair manual) to both sides of the welding flange.
- Prime the weld area on inside and outside before sealing.
- ♦ Apply sealant only to primed panels.
- Completely seal panel overlap, panel edges, butt joints, weld seams, etc. with sealant.
- The weld seams may not be sanded otherwise the strength of the weld seam will be impaired.
- Reproduce the paint structure as described in the paint manual.
- Restoring the underbody protection with long-term underbody protective material.
- Apply protective material to all cavities in repair area after finish painting.
- Protective material must be completely applied on separation cuts (for example, in side panel).
- Open water drains after cavity sealant material dries.

14.1.1 Contact Corrosion

Contact corrosion can occur if incorrect connecting elements (bolts, nuts, washers, etc.) are used.

For this reason, only fasteners with a special surface coating may be installed.

Furthermore, only rubber/plastic parts and adhesive made of electrically non-conductive materials are used.

If there are doubts about the suitability of parts, use new parts.

14.2 Sealing Cavities

The corrosion protection used in production is described in the general and vehicle-specific ⇒ Paint Manual.



Note

- ♦ Before beginning the process, it is required to become familiar with the safety information sheet covering safety precautions and safety recommendations.
- Even if products are not subject to labels, the general safety precautions for chemical products must be followed.

•



Note

Depending on the type of cavity being treated, the drying process may take more than several days. Sufficient ventilation must be ensured during the drying process.



Note

- Function components such as brake and exhaust systems may not be sprayed.
- Rubber and plastic components should likewise also not be sprayed.

Cleaning

- Any dripping cavity sealant can be easily wiped away.
- Adhesive remover should be used to clean off any drips on material.
- For large surfaces, a steam blaster may be used for cleaning. Splashes on painted surfaces should be removed immediately.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



15 Plastic Repair

- ⇒ S15.1 ervicing", page 71
- ⇒ S15.2 ervicing", page 73
- ⇒ S15.3 ervicing, Up to 100 mm Long", page 74
- ⇒ S15.4 ervicing, Up to 30 mm Diameter", page 75
- ⇒ R15.5 epair (GFK)", page 76



Note

Follow the general accident prevention tips. Do not repair safety-related components whose function can no longer be guaranteed after servicing, for example, those that absorb impact.

Plastic repairs with the plastic repair kit refer to servicing painted plastic body components such as the bumper and mirror housing. Before repairing, check carefully to see if the service can be performed and if it makes sense economically (repair/new part).

Plastic components with a structured surface can be serviced. However, the quality standard of the surface will not be at the same level as that of a new part.


15.1 Dents, Servicing



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.






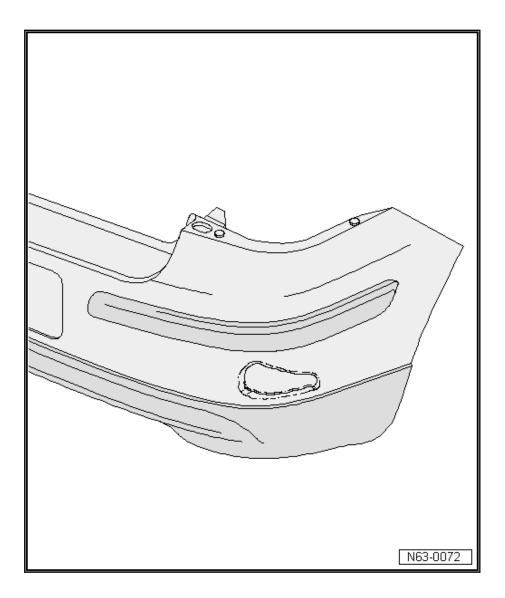

- First clean and dry the repair part.
- Warm the dented area with a hot air gun until it can be pressed out with a suitable tool.
- Now sand the dented area with 120 grit sandpaper.
- Then clean the repair area with cleaner. Flash-off time is five minutes.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Now any uneven areas can be filled with adhesive and smoothed out with a spatula.
- Curing can be accelerated with an infrared heater. Set it for 15 minutes at 60° - 70° C (140-158 °F).
- Now sand the repair location down with 120 grit sandpaper.
- Now remove the sanding dust.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Create the paint structure according to the paint repair man-

15.2 Scratches, Servicing

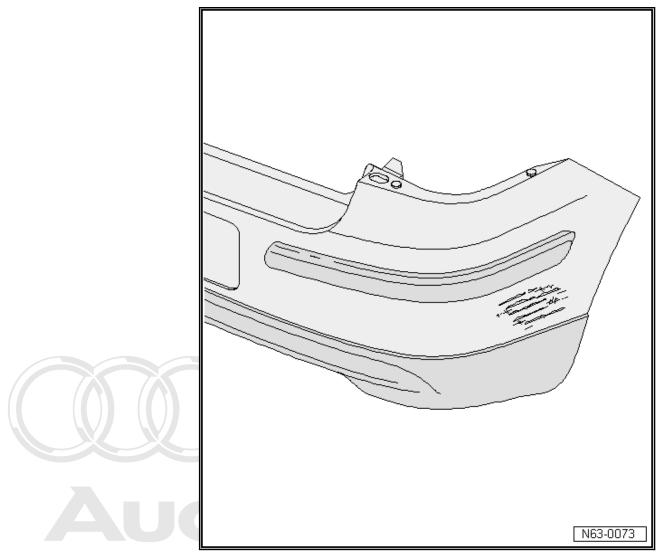


Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respeirs clean and dryotheirepair partent. Copyright by AUDI AG.

- in responde creativation any entropic open quarter a copyright by need in
- Remove stuck material with 80 grit sandpaper.
- Then clean the repair area with cleaner. Flash-off time is five minutes.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Now any uneven areas can be filled with adhesive and smoothed out with a spatula.
- Curing can be accelerated with an infrared heater. Set it for 15 minutes at 60°-70 °C (140-158 °F).
- Now sand the repair location down with 120 grit sandpaper.
- Now remove the sanding dust.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Create the paint structure according to the paint repair manual.




15.3 Cracks, Servicing, Up to 100 mm Long

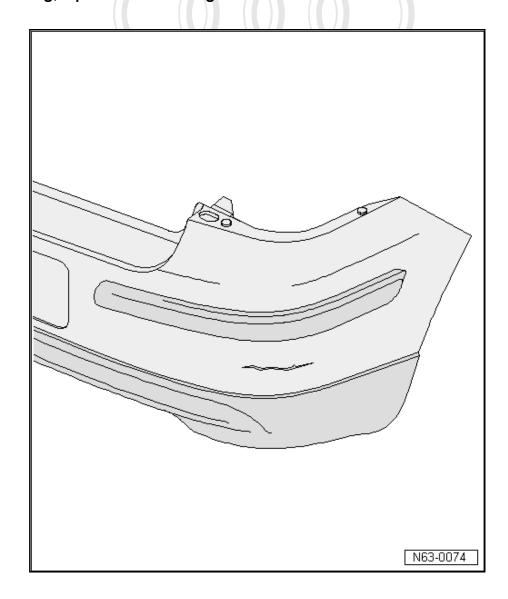

- First clean and dry the repair part.
- Uneven areas can be removed through expanding by drilling the crack (5 mm) and sanding it in a V-formation.
- Then clean the repair area with cleaner. Flash-off time is five minutes.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- First, install a reinforcement mat on the back of the repair part using adhesive so that it overlaps the damaged parts by at least 20 mm.
- Curing can be accelerated with an infrared heater. Set it for 15 minutes at 60°-70 °C (140-158 °F).
- Then, the front side of the sanded area can be filled with adhesive and smoothed with a spatula.
- Curing should be accelerated on the front side with the infrared heater as explained earlier.
- Now sand the repair location down with 120 grit sandpaper.

- Now remove the sanding dust.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Create the paint structure according to the paint repair man-

15.4 Holes, Servicing, Up to 30 mm Diameter

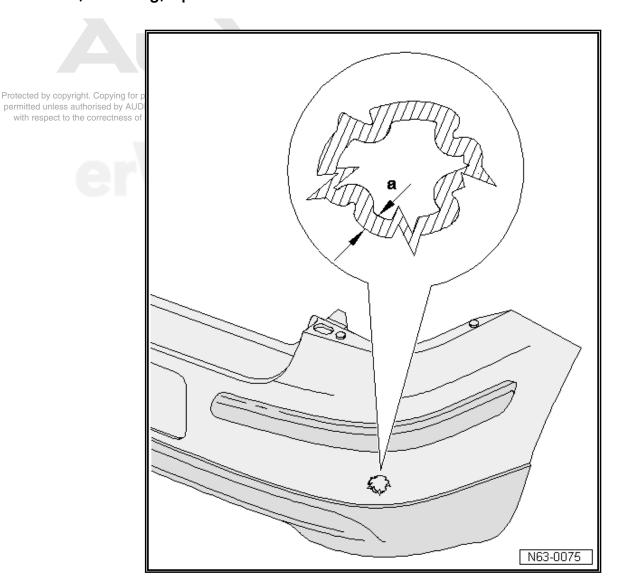


- First clean and dry the repair part.
- Using 120 grit sandpaper, sand the repair location in a funnel shape 10-20 mm, dimension a.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Then rough up the area with 120 grit sandpaper.
- Then clean the repair area with cleaner. Flash-off time is five minutes.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.

- First, install a reinforcement mat on the back of the repair part using adhesive so that it overlaps the damaged parts by at least 20 mm.
- Curing can be accelerated with an infrared heater. Set it for 15 minutes at 60°-70 °C (140-158 °F).
- Then, the front side of the sanded area can be filled with adhesive and smoothed with a spatula.
- Curing should be accelerated on the front side with the infrared heater as explained earlier.
- Now sand the repair location down with 120 grit sandpaper.
- Now remove the sanding dust.
- Now spray lightly with bonding agent and allow 10 minutes flash-off time.
- Create the paint structure according to the paint repair manual.

15.5 Plastic Repair (GFK)

- ⇒ C15.5.1 rack Repair Procedure, Servicing", page 77
- ⇒ S15.5.2 urface Damage Repair Procedure, Servicing", page 79

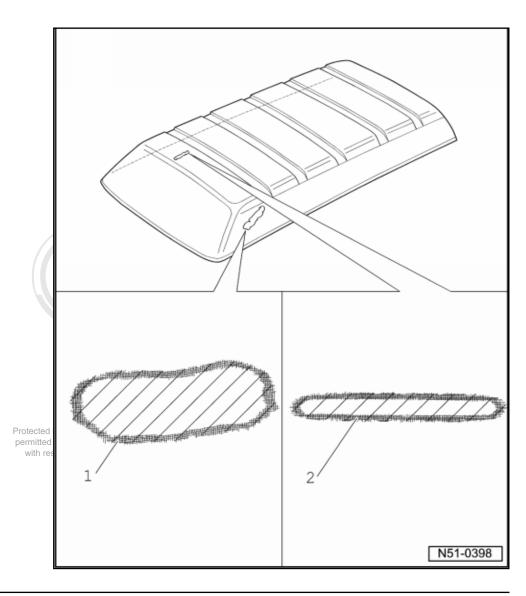



Note

Follow the general accident prevention tips. Do not repair safety-related components whose function can no longer be guaranteed after servicing, for example, those that absorb impact.


- 1- Crack
- ◆ Fiber glass mat, polyester resin and hardener
- 2- Surface damage
- ♦ Fiber glass reinforced polyester resin, hardener



Note

Follow the usage instructions from the manufacturer when working with the materials.

15.5.1 "Crack" Repair Procedure, Servicing

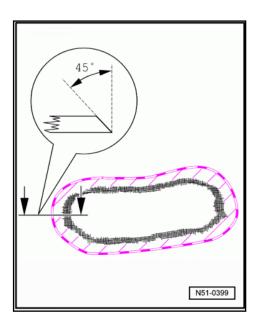


 Sand off the edge of the crack all around at approximately a 45° angle.




Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

Sand the surface down approximately 100 mm all around the crack -shaded area- with 150 grit sandpaper and clean with silicone remover.





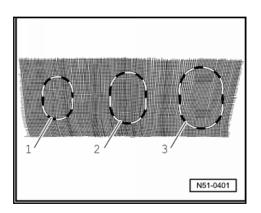

Cut the three fiber glass mats: -1- approximately 25 mm overlapping the crack, -2- approximately 50 mm overlapping, -3- approximately 75 mm overlapping.




Note

With larger cracks, creating a support from styrofoam is recommended. Wrap the styrofoam with plain, commercially available PE plastic film to avoid contact with polyester resin. Then secure the finished support on the inside of the crack with adhesive tape.


Install the fiber glass mats

Protected by copyright. Copying for private permitted unless authorised by AUDI AG. with respect to the correctness of inform




- Mix the polyester resin (follow the manufacturer's instruc-
- Apply the polyester resin lightly to the crack.
- Saturate the smallest fiber glass mat -1- with polyester resin and apply to the crack -4-.
- Remove air bubbles in the polyester resin with a pointed tool immediately after applying.
- After hardening, sand the material applied with 120 grit sandpaper.
- Clean the repair location with silicone remover.
- Repeat the procedure with the second -2- and third -3- fiber glass mats.

15.5.2 "Surface Damage" Repair Procedure, Servicing

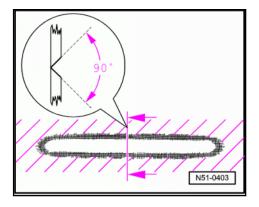

- Grind down the surface damage in a V-shape.
- Sand the surface approximately 50 mm all around the surface damage -shaded area- with 150 grit sandpaper.
- Clean the repair location with silicone remover.

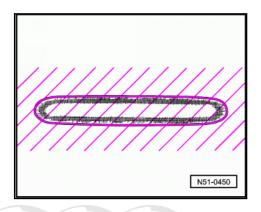

- Mix fiber glass reinforced polyester resin (follow the manufacturer's instructions) and apply it to the repair location-shaded area-.
- After curing, sand down the repair location and clean with silicone remover.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.





16 Glass Repair

- ⇒ R16.1 epair", page 80
- ⇒ S16.2 pecial Tools and Testing Equipment", page 84
- ⇒ D16.3 escription", page 86


16.1 Windshield Repair

Aside from replacing bonded windshields, there is the less expensive option of repairing a windshield that has been damaged by a stone, under certain conditions.

Tinted windshields, windshields with colored liners or tinted glass, and windshields with a heat function can also be repaired, because the tint and heat are emitted by the PVB inter-

Repairing the wingleded by copyright Copyring for private or commercial purposes, in part or in whole, is not full the wingle of the copyring the copyring the wingle of the copyring the wingle of the copyring the copyri following conditions: the respect to the correctness of information in this document. Copyright by AUDI AG.


- It is legally prohibited to repair within the visual field of the driver. This is understood as 290 mm wide strips, parallel to the center of the vehicle longitudinal axis, going out from the center of the steering wheel, and bordered by the upper and lower edge through the wiper field.
- The damaged area must not be larger than 25 mm in diame-
- The windshield must not have more than three damaged areas.
- Only damage on the outer edges of the window can be repaired. The inside of the window and the intermediate plastic film must not have any damage. Chippings on the windshield glass are not stone impacts and therefore can also not be repaired.
- If no (visible) moisture or dirt is in the damaged location.
- The damage location must not lie within the driver's direct field of vision -1-. This field corresponds to a strip approximately 29 cm wide (DIN A4 format across) central to the driver's line of sight in direction of travel, bordered above and below by the windshield washer field.
- Cracks radiating out from the damage location must not be longer than 50 mm and/or continue outward into the peripheral area.
- The damaged location and/or cracks must be at least 10 cm away from the window edge.

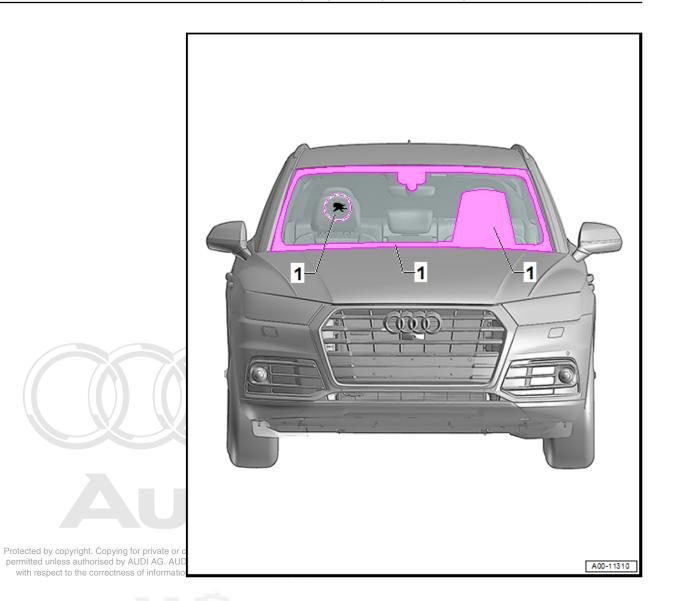


16.1.1 Requirements

The following damage may be repaired as long as it is not in the field of vision or in the peripheral areas of the windshield:

Bullseye

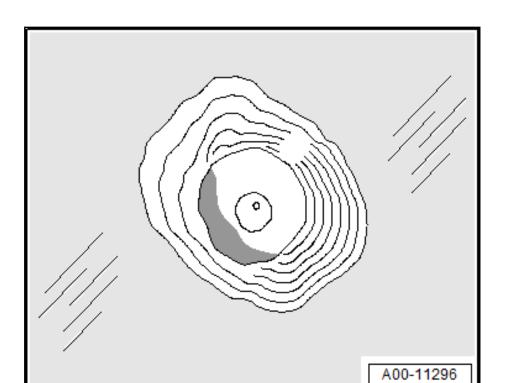


Star break

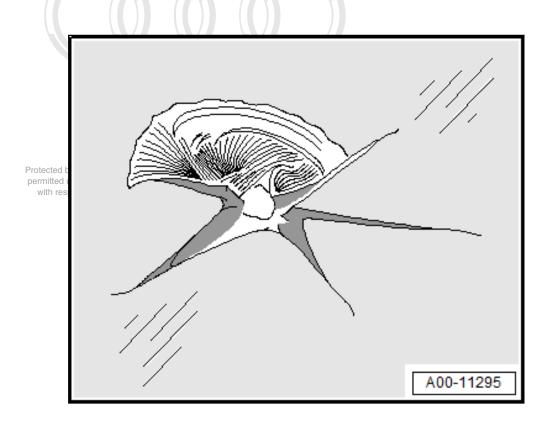


Combination



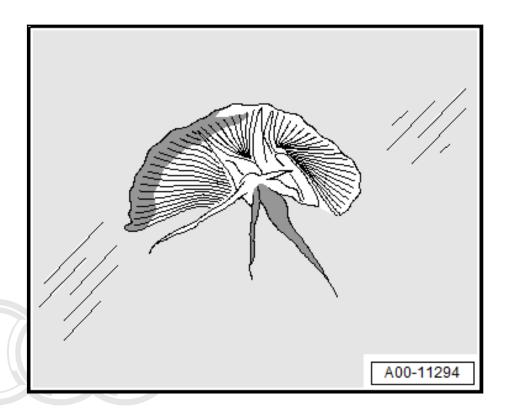

Half moon

Protected by copyright. Copying for private permitted unless authorised by AUDI AG. with respect to the correctness of inform

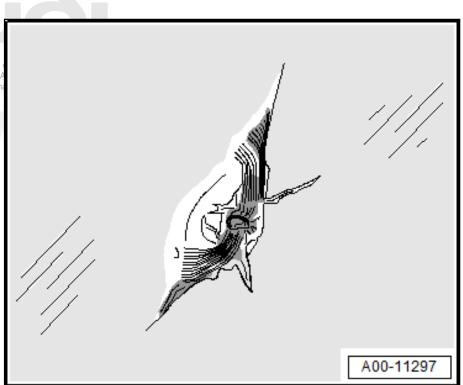



16.1.2 **Repair Description**



Note

- After the repair, the vehicle is ready to operate again without any waiting time.
- Traces of fractures cannot be removed completely with many types of breaks but they do not affect the results of the repair.
- After repair, the window is as strong as normal and further cracks are prevented by the molded and hardened plastic resin. The hardened resin is colorless and has the same refractive index as glass.

16.2 Required Special Tools and Testing **Equipment**

Windscreen Repair Set -VAS6092A-


Contains the following tools:



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



- 1 Quantity: 3 Repair Resin - approximately 10 repairs per pack
- 2 Finishing Resin for sealing the stone impact
- 3 Quantity: 10 Scraper **Blades**

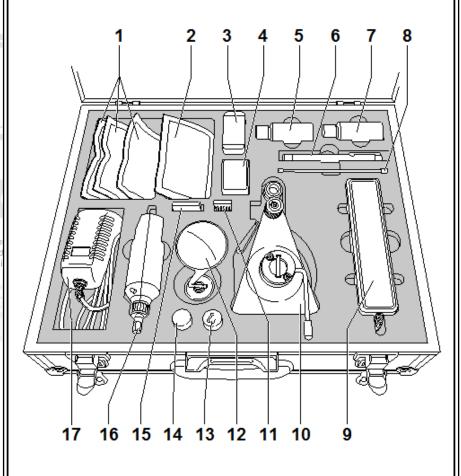

Protected by copyright. Copying for private or comm permitted unless authorised by AUDI AG. AUDI AG with respect to the correctness of information in the



Note

Only use the correct and undamaged scrapers.

- 4 Hardening Film
- 5 Vacuum Gel
- 6 Polish
- 7 Mini Lamp
- 8 Carbide Pin
- 9 LED UV Lamp to harden the stone impact
- 10 Tool Holder
- 11 Quantity 2x Glass Drill Milling Cutter 1.2 mm
- 12 Scraper Blade Holder
- 13 Magnification Mirror
- 14 Polishing Head
- 15 Stone Chip Finder
- 16 Drill

A00-11311



17 - Volt Cable (Cigarette Lighter Cable)


16.3 Repair Description

- Repairs should not take place in direct sunlight.
- The repair location must be approximately at room tempera-
- The work area must be protected against moisture.

Cleaning


- Use the glass cleaner to clean the window glass around the damage location without wiping over the point of impact.
- Remove any loose glass chips and contamination in the stone impact using the carbide pin, but do not enlarge the gouge unnecessarily.

The more glass, that is missing on the surface, the stronger the coept any liability visual effects of the repair will be so of information in this document. Copyright by AUDI AG.



Inspection Mirror, Securing

Secure the inspection mirror -2- from the interior on the window glass to that the procedure can be watched from the outside.

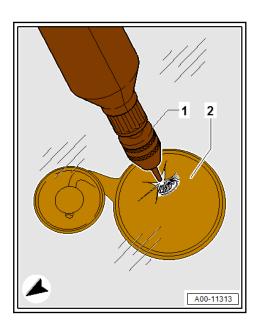

Drilling




Note

Always hold the drill with two hands! This is the only way to insure the exact positioning of the hole. Overheating the drill can be prevented by short breaks when drilling (every 2 seconds).

- Remove any possible moisture with suction hooks while helping with hair dryer from inside. Stop the repair if moisture cannot be removed.
- Insert the carbide drill bit in the drill -1- and drill a 1 mm deep hole in the center of the damage location vertical to the window glass. The drill depth is reached when the ball of the drill meets the glass.




Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.

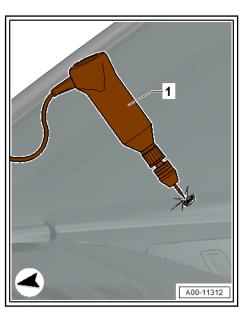

Tool Holder, Securing

Coat the suction area of the tool holder with vacuum gel.
 This allows a position correction of the secured tool holder.
 By placing the suction cup lever toward the rear, the tool holder is secure on the window glass so that the injector hole is located exactly over the damage location.

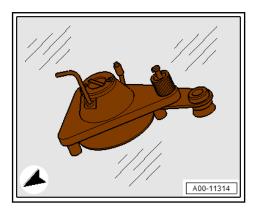


Injector, Filling

Remove the piston approximately 4 to 5 mm from the cylinder. Fill the working chamber of the injector -2- completely without bubbles with repair resin.

The repair resin -1- is hardened by UV and most for this reason be protected from UV rays.

- Wait until resin flows into the rubber seal.

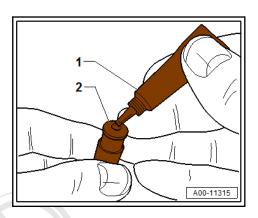


Injector, Positioning (Pressure Phase)

- Install the pistons -2- from the injectors -1- in the cylinder until it can be seen in the inspection mirror how the opening of the seal slightly (approximately 1 cm) enlarges. Pressure is created through the working chamber and the repair resin is pressed into the damage location. The air is now sealed at the stone impact. This can be seen by the black air pocket getting smaller. In the inspection mirror it can be seen which damage location is filled with repair resin and becomes transparent again.
- Note in mirror when the damage location is filled. Then end injection.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not Stay in this position for some mitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.







Note

The resin penetrates into the cracks very slowly and may not be visible right away.



Note

To high of work pressure can lead to damage by lengthening the cracks or lifting the foil on old stone impacts or stone impacts with the formation of cracks.


Finishing resin - hardening film

 Cut an approximately 4 to 5 cm long piece of the foil using the blade.



- Turn the injector piston up to 5 mm in the cylinder. Now remove the tool holder and the suction cup lever around it and slightly lift the suction cup from the window glass.
- Place the hardening film without pressure from the bottom upward on the repair location, immediately after removing the tool holder.
- Lift the harding foil -1- from above slightly (until slightly under the crater), place a drop of finish hardener directly on the impact point and let the hardening foil return to position on the window glass.

If there are now small bubbles between the hardening foil and the window glass, remove it, by lifting the hardening foil again lightly from above and then the push the air out of the finish hardener.

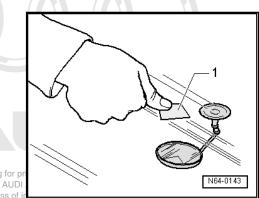


Protected by copyright. Copying for p permitted unless authorised by AUDI with respect to the correctness of

Immediately return injector to packaging because resin is UV sensitive and can be reused for the next repair. Replace the tool carrier in the released position in case and remove mirror with mount.

Resin, Hardening

Secure the UV lamp -1-, after rubbing the suction cup with vacuum gel, from the outside over the repair damage location and switch it on.

Harding the damage location is completed after approximately 10 minutes and the UV lamp can be removed from the window glass.

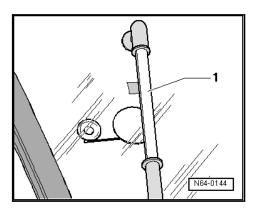


Final Treatment

- Scraping
- Remove the hardening film from the repair location. Hold the blade -1- at a 90° to the window glass and scrape the excess material from the damage location. The scraped resin is matte. If there are still shiny locations or a recess is

present, finish resin must be applied, hading foil positioned and scarped again to ensure a correct flat surface.

Do not push or bend up because this can lead to it being pulled out of the damage location.

Only use the correct and undamaged blades.

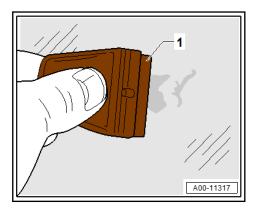



Note

- After the repair, the vehicle is ready to operate again without any waiting time.
- Traces of fractures cannot be removed completely with many types of breaks but they do not affect the results of the repair.
- After repair, the window is as strong as normal and further cracks are prevented by the molded and hardened plastic resin. The hardened resin is colorless and has the same refractive index as glass.



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



17 Thread Repairs

- ⇒ R17.1 epairs on Safety-Related Components", page 91
- ⇒ o17.2 n Subframe Fastener, Servicing", page 91
- ⇒ P17.3 lus Twinsert", page 98

If damaged threads are repaired, inserts with zinc-nickel coating must be used.

Steel shavings from drilling must be removed completely.

Only replace threaded pins with original parts.

Damaged threads can be repaired with thread inserts with zincnickel coating.



Note

Contact corrosion is prevented only by using this coating.

Some threads are already supplied with thread inserts at the factory.

17.1 Thread Repairs on Safety-Related Components

Depending on the vehicle-specific structure characteristics, repairs to threads such as axle or seat belt mounts are permitted are not feasible.

RO: 50 79 49 50

17.2 Threads on Subframe Fastener, Servicing



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability **Note**th respect to the correctness of information in this document. Copyright by AUDI AG.

The thread repair on this vehicle is described for the subframe in the example. It is identical for the other mounts.

17.2.1 Tools

Special tools and workshop equipment required

- ◆ Thread Repair Kit M8 x 20
- ♦ Thread Repair Kit M10 x 25
- ♦ Thread Repair Kit M12 x 30
- ◆ Thread Repair Kit M14 x 35
- Thread Repair Kit A7/16 x 21,6
- Pneumatic Brush Grinder Set -VAS6446A-

Drill - 1100 Watt -VAS6267 A-



Replacement Part


♦ Isopropyl Alcohol



Note


Use tools approved by AUDI AG for performing repair work correctly.

1 - Heli-Coil Insert

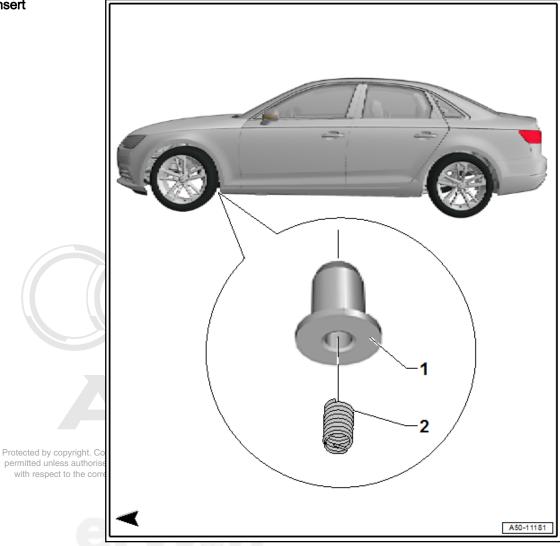

Thread Repair Set Contents


- 1 Spiral Bit
- 2 Thread Tap
- 3 Installation Spindle
- 4 Threaded Insert
- 5 Tang Break-Off Tool with Magnetic Tip

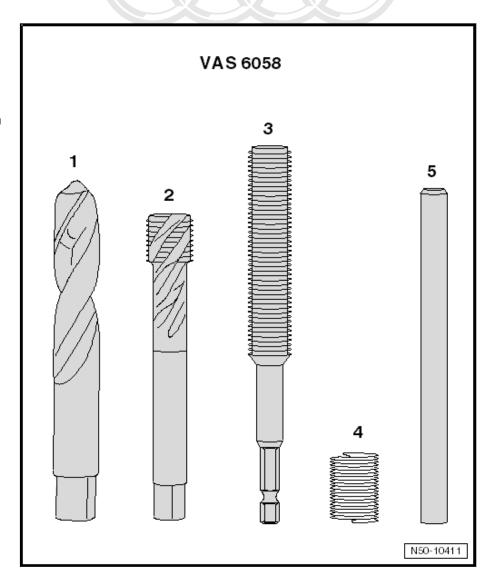

Thread, Servicing

Thread, Drilling

- Drill out the threads using the spiral bit.

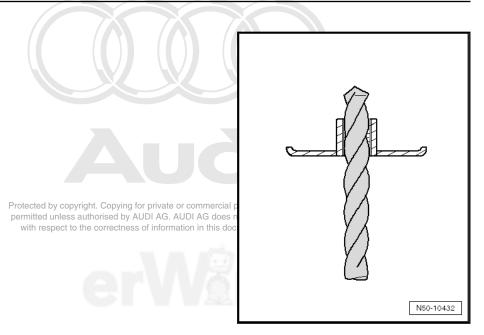



CAUTION

Risk of injury due to flying metal shavings. Irritation and injury to skin and eyes possible.


- Wear protective eyewear.
- Wear safety gloves.



Note


- Use the Drill 1100 Watt -VAS6267A- for drilling and grinding.
- When drilling, the drill must be held by a second technician using an additional handle.
- Do not tilt the drill.



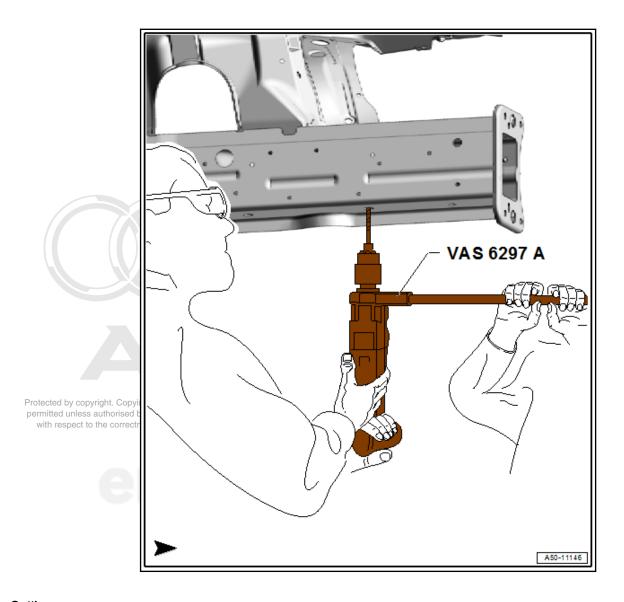


Threads, Cutting

- Cut the threads with the thread tap.

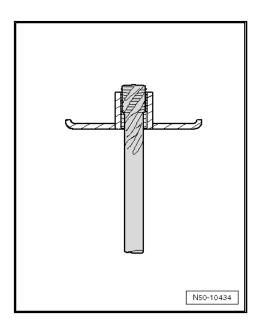

Threaded Insert, Inserting

Turn the threaded insert -3- onto the installation spindle until the driving pin -2- makes contact on the drive tab -1- of installation spindle.

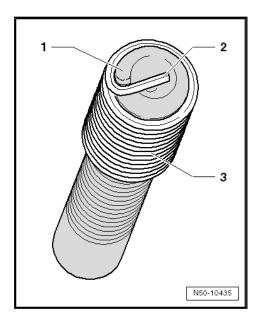

Clean the threaded bushing (blow with compressed air).



Note


The threaded insert must be able to turn easily.

Screw the threaded insert into the threaded plate until the threaded insert is flush with the outside of the threaded plate (visual inspection).



Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.




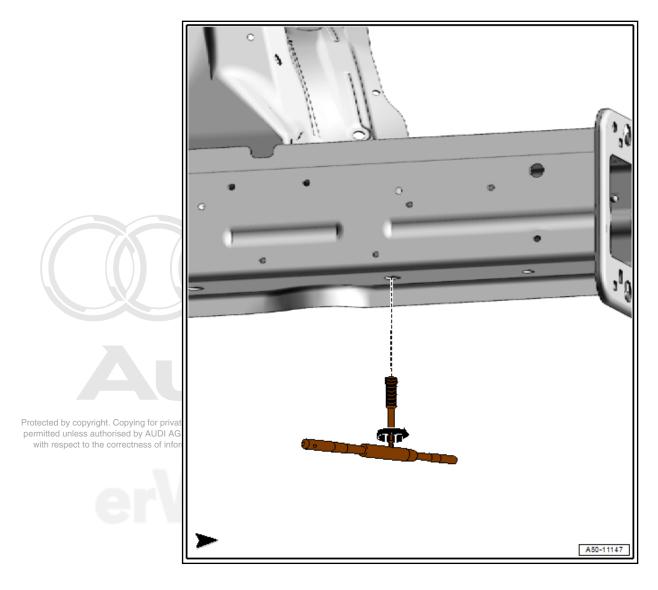

- Then tighten the threaded insert an additional 1/4 turn in-
- Remove the installation spindle.
- Break off the threaded insert drive pin using the pin breaker.





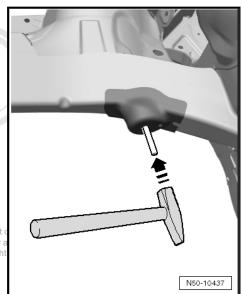

17.3 **Helicoil Plus Twinsert**

Thread repair sets

VAS271 001

- ♦ M8 x 16 mm
- Threaded Insert -WHT 009 793-

VAS271 003

- ♦ M10 x 20 mm
- Threaded Insert -WHT 009 796-

VAS271 005

- M12 x 1.5 x 24 mm
- ♦ Threaded Insert -WHT 009 794-


VAS271 007

- ♦ M14 x 1.5 x 28 mm
- ♦ Threaded Insert -WHT 009 795-

VAS271 009

- 7/16-20UNF x 22.2 mm
- Threaded Insert -WHT 009 802-

The HELICOIL® Plus Twinsert consists of two HELICOIL® Plus threaded inserts and is used when threaded holes are torn out. The outer part is a HELICOIL® Plus Free Running. The inner insert can be chosen as needed, as a HELICOIL® Plus Free Running or HELICOIL® Plus® Screwlock.

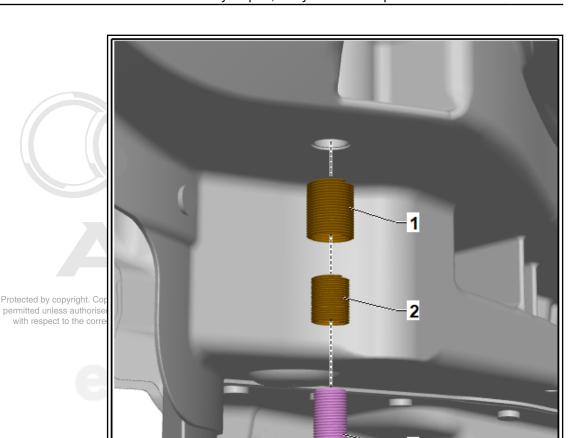


- ⇒ T17.3.1 hreaded Insert, Removing", page 99
- ⇒ H17.3.2 ole, Drilling", page 100
- ⇒ T17.3.3 apping", page 101
- ⇒ I17.3.4 nsert, Inserting", page 102
- ⇒ 117.3.5 nserting", page 103
- ⇒ B17.3.6 reaking", page 104
- ⇒ I17.3.7 nsert, Inserting", page 105
- ⇒ 117.3.8 nserting", page 106
- ⇒ B17.3.9 reaking", page 106

17.3.1 Faulty Threaded Insert, Removing

Remove the faulty threaded insert using a commercially available needle nose pliers.

A00-11384

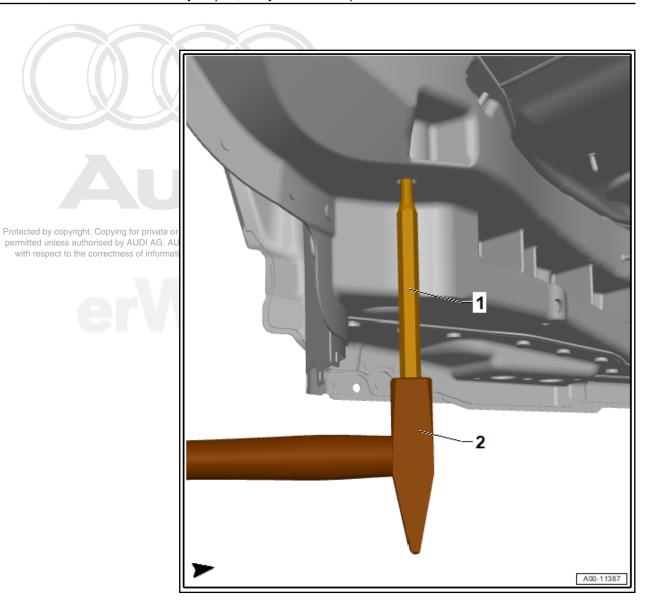

Core Hole, Drilling 17.3.2




CAUTION

There is a risk of injury from tilting the drill.

- Use the Drill -VAS6297- for drilling.
- Do not tilt the drill.
- Use the core hole drill from the respective thread repair kit and drill with the drill.


Clean the core hole using the Cleaning Solution -D 009 401 04-.

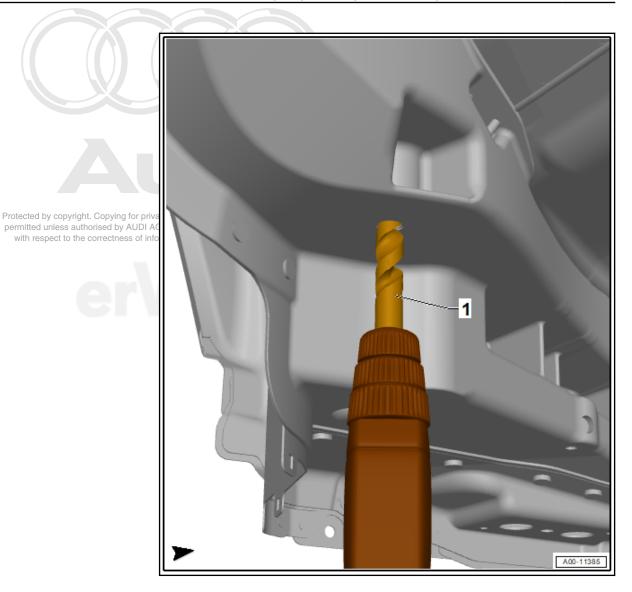

17.3.3 Thread, Tapping


 From the respective thread repair kit, tap the threads with the thread tap.

Clean the threads using the Cleaning Solution -D 009 401 04-.

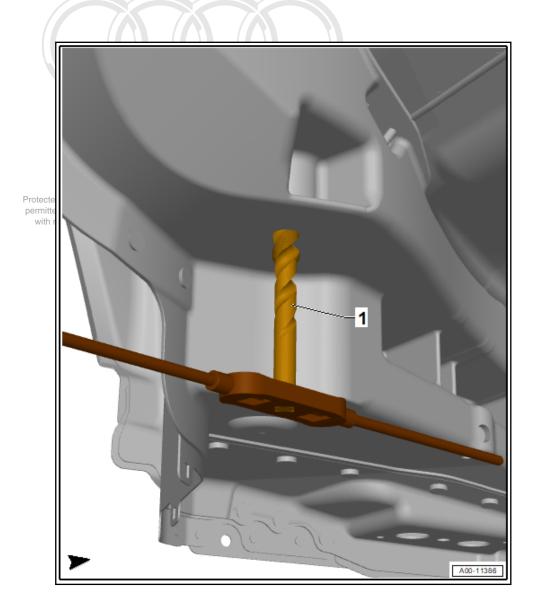

17.3.4 Threaded Insert, Inserting

Turn the threaded insert -3- onto the installation spindle until the driving pin -2- makes contact on the drive tab -1- of installation spindle.

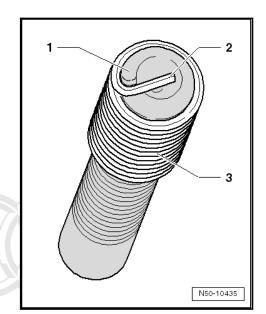


17.3.5 Threads, Inserting

- Clean the threaded bushing (blow with compressed air).
- Screw the threaded insert into the threaded plate until the
 threaded insert is flush with the outside of the threaded plate
 (visual inspection).
- with respect to the correctness of information in this document. Copyright by AUDI AG.

 Then tighten the threaded insert an additional ¹/₄ turn inward.
- Remove the installation spindle.

Clean the threads using the Cleaning Solution -D 009 401 04-.

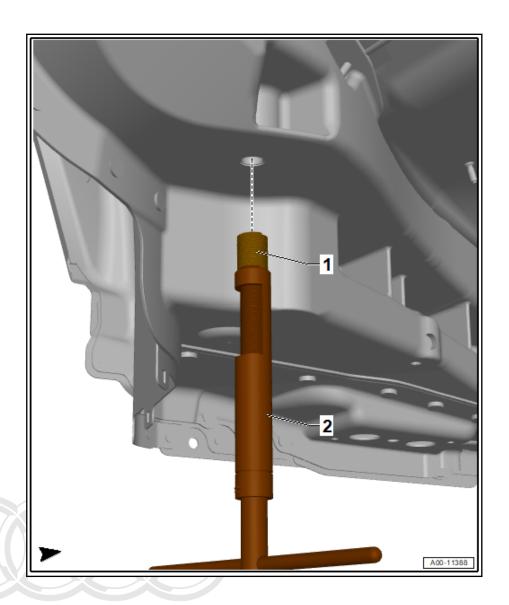


17.3.6 Pin, Breaking

- Break off the threaded insert drive pin using the pin breaker.

Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability with respect to the correctness of information in this document. Copyright by AUDI AG.



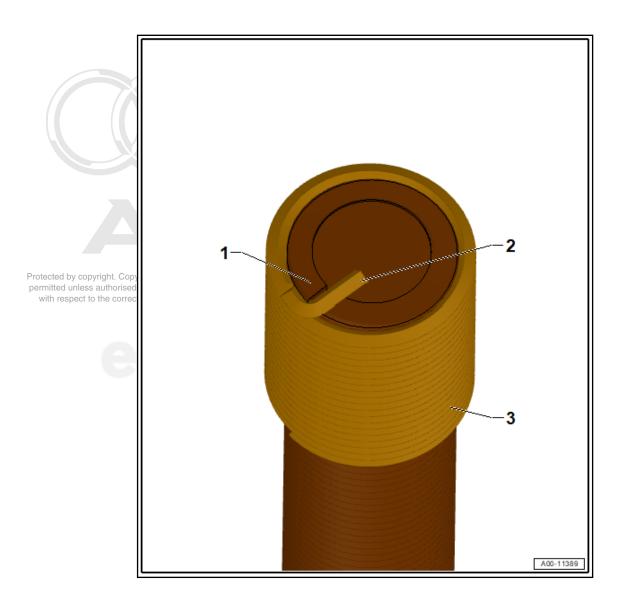


17.3.7 Threaded Insert, Inserting

 Turn the threaded insert -3- onto the installation spindle until the driving pin -2- makes contact on the drive tab -1- of installation spindle.





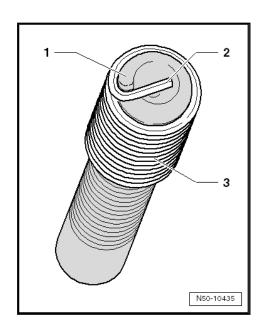

17.3.8 Threads, Inserting


- Clean the threaded bushing (blow with compressed air).
- Screw the threaded insert into the threaded plate until the threaded insert is flush with the outside of the threaded plate p(VISUAL INSPECTION) by AUDI AG. AUDI AG does not guarantee or accept any liability
- with respect to the correctness of information in this document. Copyright by AUDI AG. Then tighten the threaded insert an additional ¹/₄ turn inward.
- Remove the installation spindle.

17.3.9 Pin, Breaking

- Break off the threaded insert drive pin using the pin breaker.

Clean the threads using the Cleaning Solution -D 009 401 04-.



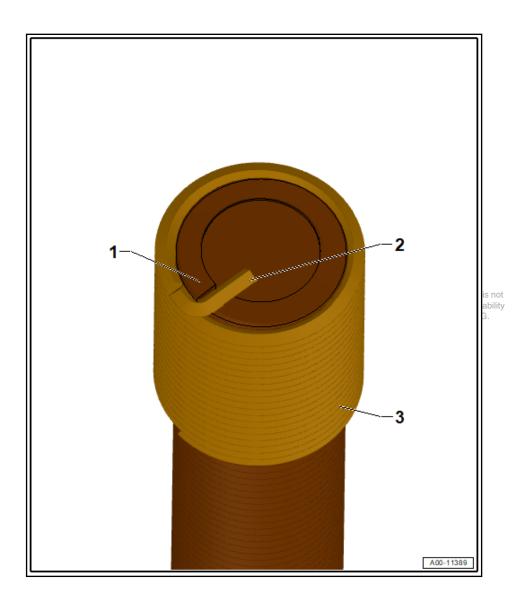

Cautions & Warnings

Please read these WARNINGS and CAUTIONS before proceeding with maintenance and repair work. You must answer that you have read and you understand these WARNINGS and CAUTIONS before you will be allowed to view this information.

- If you lack the skills, tools and equipment, or a suitable workshop for any procedure described
 in this manual, we suggest you leave such repairs to an authorized Audi retailer or other
 qualified shop. We especially urge you to consult an authorized Audi retailer before beginning
 repairs on any vehicle that may still be covered wholly or in part by any of the extensive
 warranties issued by Audi.
- Disconnect the battery negative terminal (ground strap) whenever you work on the fuel system
 or the electrical system. Do not smoke or work near heaters or other fire hazards. Keep an
 approved fire extinguisher handy.
- Audi is constantly improving its vehicles and sometimes these changes, both in parts and specifications, are made applicable to earlier models. Therefore, part numbers listed in this manual are for reference only. Always check with your authorized Audi retailer parts department for the latest information.
- Any time the battery has been disconnected on an automatic transmission vehicle, it will be necessary to reestablish Transmission Control Module (TCM) basic settings using the Audi Factory Approved Scan Tool (ST).
- Never work under a lifted vehicle unless it is solidly supported on stands designed for the
 purpose. Do not support a vehicle on cinder blocks, hollow tiles or other props that may
 crumble under continuous load. Never work under a vehicle that is supported solely by a jack.
 Never work under the vehicle while the engine is running.
- For vehicles equipped with an anti-theft radio, be sure of the correct radio activation code before disconnecting the battery or removing the radio. If the wrong code is entered when the power is restored, the radio may lock up and become inoperable, even if the correct code is used in a later attempt.
- If you are going to work under a vehicle on the ground, make sure that the ground is level.
 Block the wheels to keep the vehicle from rolling. Disconnect the pattery negative terminal (ground strap) to prevent others from starting the vehicle while you are under it.
- Do not attempt to work on your vehicle if you do not feel well. You increase the danger of
 injury to yourself and others if you are tired, upset or have taken medicine or any other
 substances that may impair you or keep you from being fully alert.
- Never run the engine unless the work area is well ventilated. Carbon monoxide (CO) kills.
- Always observe good workshop practices. Wear goggles when you operate machine tools or work with acid. Wear goggles, gloves and other protective clothing whenever the job requires working with harmful substances.
- Tie long hair behind your head. Do not wear a necktie, a scarf, loose clothing, or a necklace
 when you work near machine tools or running engines. If your hair, clothing, or jewelry were to
 get caught in the machinery, severe injury could result.

Cautions & Warnings

- Do not re-use any fasteners that are worn or deformed in normal use. Some fasteners are
 designed to be used only once and are unreliable and may fail if used a second time. This
 includes, but is not limited to, nuts, bolts, washers, circlips and cotter pins. Always follow the
 recommendations in this manual replace these fasteners with new parts where indicated,
 and any other time it is deemed necessary by inspection.
- Illuminate the work area adequately but safely. Use a portable safety light for working inside or under the vehicle. Make sure the bulb is enclosed by a wire cage. The hot filament of an accidentally broken bulb can ignite spilled fuel or oil.
- Friction materials such as brake pads and clutch discs may contain asbestos fibers. Do not create dust by grinding, sanding, or by cleaning with compressed air. Avoid breathing asbestos fibers and asbestos dust. Breathing asbestos can cause serious diseases such as asbestosis or cancer, and may result in death.
- Finger rings should be removed so that they cannot cause electrical shorts, get caught in running machinery, or be crushed by heavy parts.
- Before starting a job, make certain that you have all the necessary tools and parts on hand.
 Read all the instructions thoroughly, do not attempt shortcuts. Use tools that are appropriate to the work and use only replacement parts meeting Audi specifications. Makeshift tools, parts and procedures will not make good repairs.
- Catch draining fuel, oil or brake fluid in suitable containers. Do not use empty food or beverage containers that might mislead someone into drinking from them. Store flammable fluids away from fire hazards. Wipe up spills at once, but do not store the oily rags, which can ignite and burn spontaneously.
- Use pneumatic and electric tools only to loosen threaded parts and fasteners. Never use these
 tools to tighten fasteners, especially on light alloy parts. Always use a torque wrench to tighten
 fasteners to the tightening torque listed.
- Keep sparks, lighted matches, and open flame away from the top of the battery. If escaping hydrogen gas is ignited, it will ignite gas trapped in the cells and cause the battery to explode.
- Be mindful of the environment and ecology. Before you drain the crankcase, find out the
 proper way to dispose of the oil. Do not pour oil onto the ground, down a drain, or into a
 stream, pond, or lake. Consult local ordinances that govern the disposal of wastes.
- The air-conditioning (A/C) system is filled with a chemical refrigerant that is hazardous. The
 A/C system should be serviced only by trained automotive service technicians using approved
 refrigerant recovery/recycling equipment, trained in related safety precautions, and familiar
 with regulations governing the discharging and disposal of automotive chemical refrigerants.
- Before doing any electrical welding on vehicles equipped with anti-lock brakes (ABS), disconnect the battery negative terminal (ground strap) and the ABS control module connector.
- Do not expose any part of the A/C system to high temperatures such as open flame.
 Excessive heat will increase system pressure and may cause the system to burst.

Cautions & Warnings

- When boost-charging the battery, first remove the fuses for the Engine Control Module (ECM), the Transmission Control Module (TCM), the ABS control module, and the trip computer. In cases where one or more of these components is not separately fused, disconnect the control module connector(s).
- Some of the vehicles covered by this manual are equipped with a supplemental restraint system (SRS), that automatically deploys an airbag in the event of a frontal impact. The airbag is operated by an explosive device. Handled improperly or without adequate safeguards, it can be accidentally activated and cause serious personal injury. To guard against personal injury or airbag system failure, only trained Audi Service technicians should test, disassemble or service the airbag system.
- Do not quick-charge the battery (for boost starting) for longer than one minute, and do not
 exceed 16.5 volts at the battery with the boosting cables attached. Wait at least one minute
 before boosting the battery a second time.
- Never use a test light to conduct electrical tests of the airbag system. The system must only
 be tested by trained Audi Service technicians using the Audi Factory Approved Scan Tool (ST)
 or an approved equivalent. The airbag unit must never be electrically tested while it is not
 installed in the vehicle.
- Some aerosol tire inflators are highly flammable. Be extremely cautious when repairing a tire
 that may have been inflated using an aerosol tire inflator. Keep sparks, open flame or other
 sources of ignition away from the tire repair area. Inflate and deflate the tire at least four times
 before breaking the bead from the rim. Completely remove the tire from the rim before
 attempting any repair.
- When driving or riding in an airbag-equipped vehicle, never hold test equipment in your hands or lap while the vehicle is in motion. Objects between you and the airbag can increase the risk of injury in an accident.
 Protected by copyright. Copying for private or commercial purposes, in part or in whole, is not permitted unless authorised by AUDI AG. AUDI AG does not guarantee or accept any liability

I have read and I understand these Cautions and Warnings.

with respect to the correctness of information in this document. Copyright by AUDI AG.